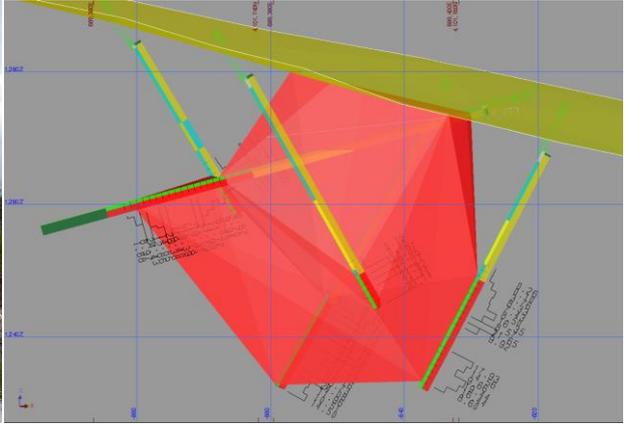


**TECHNICAL REPORT****MINERAL RESOURCE ESTIMATE – MUGLA CHROMITE DEPOSIT  
LICENSE 200712070, MUGLA PROVINCE, TURKEY**

---

**Prepared:****Florian Lowicki**  
Pr.Sci.Nat Geol. (SACNASP)  
*Resource Geologist*

---

**Reviewed and  
Approved:****Dr. Ernst-Bernhard Teigler**  
Pr.Sci.Nat Geol. (SACNASP)  
*Principal Geologist***For:****HASAT BNO GRUP GIDA YEMEK HAYV. TEKS. INS. SAN. TIC A.S.****Effective Date:** 26 February 2018**Reference:** GEE5-2016-01041

## TABLE OF CONTENTS

<b>1</b>	<b>EXECUTIVE SUMMARY .....</b>	<b>10</b>
<b>2</b>	<b>INTRODUCTION .....</b>	<b>11</b>
<b>3</b>	<b>RELIANCE ON OTHER EXPERTS .....</b>	<b>12</b>
<b>4</b>	<b>PROPERTY DESCRIPTION AND LOCATION .....</b>	<b>12</b>
<b>5</b>	<b>ACCESSIBILITY, CLIMATE, LOCAL RESOURCES, INFRASTRUCTURE AND PHYSIOGRAPHY.....</b>	<b>14</b>
<b>6</b>	<b>HISTORY .....</b>	<b>15</b>
<b>7</b>	<b>GEOLOGICAL SETTING AND MINERALIZATION .....</b>	<b>16</b>
<b>7.1</b>	<b>GENERAL .....</b>	<b>16</b>
<b>7.2</b>	<b>REGIONAL.....</b>	<b>18</b>
<b>7.3</b>	<b>PROPERTY.....</b>	<b>21</b>
<b>8</b>	<b>EXPLORATION.....</b>	<b>24</b>
<b>9</b>	<b>DEPOSIT TYPES .....</b>	<b>26</b>
<b>10</b>	<b>TRENCHING AND DRILLING.....</b>	<b>27</b>
<b>11</b>	<b>SAMPLE PREPARATION, ANALYSES AND SECURITY .....</b>	<b>30</b>
<b>12</b>	<b>DATA VERIFICATION.....</b>	<b>32</b>
<b>12.1</b>	<b>SITE VISITS .....</b>	<b>32</b>
<b>12.2</b>	<b>STANDARD OPERATING PROCEDURES (SOPs) .....</b>	<b>33</b>
<b>12.3</b>	<b>AVAILABILITY OF DATA .....</b>	<b>33</b>
<b>12.4</b>	<b>DATA PREPARATION AND MANAGEMENT .....</b>	<b>34</b>
<b>12.5</b>	<b>DRILLING LOCATION AND ORIENTATION .....</b>	<b>34</b>
<b>12.6</b>	<b>DRILLING RECOVERY AND DIAMETER .....</b>	<b>34</b>
<b>12.7</b>	<b>GEOLOGICAL LOGGING .....</b>	<b>35</b>
<b>12.8</b>	<b>SAMPLING.....</b>	<b>37</b>
<b>12.9</b>	<b>SAMPLE PREPARATION AND ANALYSIS .....</b>	<b>37</b>

<b>12.10</b>	<b>DENSITY DETERMINATION .....</b>	<b>38</b>
<b>12.11</b>	<b>CONFIRMATION OF HISTORICAL DATA ACQUISITION .....</b>	<b>39</b>
<b>12.12</b>	<b>CONCESSION AREA .....</b>	<b>39</b>
<b>12.13</b>	<b>DIGITAL TERRAIN MODEL .....</b>	<b>40</b>
<b>12.14</b>	<b>MINED OUT AREA .....</b>	<b>40</b>
<b>12.15</b>	<b>DATA QUALITY SUMMARY.....</b>	<b>40</b>
<b>13</b>	<b>MINERAL PROCESSING AND METALLURGICAL TESTING .....</b>	<b>41</b>
<b>14</b>	<b>MINERAL RESOURCE ESTIMATES .....</b>	<b>41</b>
<b>14.1</b>	<b>GEOLOGICAL MODEL.....</b>	<b>41</b>
<b>14.2</b>	<b>STATISTICAL ANALYSIS.....</b>	<b>42</b>
<b>14.3</b>	<b>INTERPRETATION OF MINERALIZED ZONES (DOMAINS).....</b>	<b>44</b>
<b>14.4</b>	<b>WIREFRAME MODEL .....</b>	<b>46</b>
<b>14.5</b>	<b>GRADE CAPPING / COMPOSITING / BLOCK MODEL DEFINITION.....</b>	<b>54</b>
<b>14.6</b>	<b>BULK DENSITY ATTRIBUTION .....</b>	<b>54</b>
<b>14.7</b>	<b>GEOSTATISTICS / INTERPOLATION METHOD .....</b>	<b>55</b>
<b>14.8</b>	<b>RESOURCE CLASSIFICATION.....</b>	<b>55</b>
<b>14.9</b>	<b>MODEL VALIDATION .....</b>	<b>55</b>
<b>14.10</b>	<b>ESTIMATE OF MINERAL RESOURCES .....</b>	<b>56</b>
<b>15</b>	<b>MINERAL RESERVE ESTIMATES.....</b>	<b>59</b>
<b>16</b>	<b>MINING METHODS .....</b>	<b>59</b>
<b>17</b>	<b>RECOVERY METHODS .....</b>	<b>60</b>
<b>18</b>	<b>PROJECT INFRASTRUCTURE .....</b>	<b>60</b>
<b>19</b>	<b>MARKET STUDIES .....</b>	<b>60</b>
<b>20</b>	<b>ENVIRONMENTAL STUDIES, PERMITTING AND SOCIAL OR COMMUNITY IMPACT.....</b>	<b>60</b>
<b>21</b>	<b>CAPITAL AND OPERATING COSTS.....</b>	<b>60</b>

<b>22</b>	<b>ECONOMIC ANALYSIS .....</b>	<b>60</b>
<b>23</b>	<b>ADJACENT PROPERTIES .....</b>	<b>60</b>
<b>24</b>	<b>OTHER RELEVANT DATA AND INFORMATION .....</b>	<b>60</b>
<b>25</b>	<b>INTERPRETATION AND CONCLUSIONS .....</b>	<b>61</b>
<b>26</b>	<b>RECOMMENDATIONS .....</b>	<b>61</b>
<b>27</b>	<b>REFERENCES.....</b>	<b>62</b>

## LIST OF FIGURES

Figure 1. Mugla license area 200712070 (red polygon) is located appr. 50 km to the West of Mugla (Source: Google Maps).....	13
Figure 2. The license area 200712070 (red fence) is located appr. 50 km to the E of Mugla; main area of drilling activities in green circle (Source: Google Maps). ....	13
Figure 3. General view of license 200712070. ....	14
Figure 4. Access to license from the town of Mugla (Source: Google Maps).....	15
Figure 5. Climate data for Mugla.....	15
Figure 6. Distribution of the podiform chromite districts of Turkey including lateritic nickel with emphasis on host-rock lithology (Yigit, 2009). ....	17
Figure 7. The study area is located around 17 km South of the license area in a similar geological setting as given in the license area (Source: MTA, 2002. Geological Map of Turkey, Scale 1:500 000).....	18
Figure 8. Composition of chromite in the Cr/(Cr+Al) vs. Mg/(Mg+Fe <sup>2+</sup> ) diagram. Fields defined for podiform (dashed line) and stratiform (solid line) chromitites according to Dick and Bullen (1984). ....	20
Figure 9. TiO <sub>2</sub> vs. Cr# [Cr/(Cr+Al)] ratio of chromites of the Ortaca chromitites, showing the distinct fields for boninites and MORB (mid-ocean ridge basalts) (after Dick and Bullen, 1984; Arai, 1992). ....	21
Figure 10. Lithologies observed. Top right: contact between ultramafic and gabbroic rocks. Top left: contact between ultramafic and strongly altered lithology. ....	23
Figure 11: Results of the geological mapping (chromite - red dots and probable faults - dashed lines). ....	25
Figure 12: Lithological legend. ....	26
Figure 13. Typical lithological column of an ophiolite sequence (source: USGS). The red square indicates the interpreted stratigraphic position of the lithologies of interest in license 200712070.....	27
Figure 14. Proposed scheme of exploration drilling. ....	28
Figure 15. SGR02 - bulk density determination as described by ARGETEST. ....	31
Figure 16. PREP03 - sample preparation as described by ARGETEST.....	31
Figure 17. XRF-WR01 - chemical analysis on pressed powder pellets as described by ARGETEST.....	32
Figure 18. Cross plots of bulk density and Cr <sub>2</sub> O <sub>3</sub> vs. core recovery. ....	35
Figure 19. Assay results for CRMs AMIS 0387 (left) and AMIS 0388 (right) for Cr <sub>2</sub> O <sub>3</sub> . ....	38

Figure 20. Cross plot bulk density [t/m <sup>3</sup> ] vs. Cr <sub>2</sub> O <sub>3</sub> [%] showing a high scatter.....	39
Figure 21. Certificate of license 200712070.....	40
Figure 22. Ellipsoid as geometry underlying the interpretation of chromite lenses.....	42
Figure 23. Frequency plots of density and relevant chemical parameters.....	43
Figure 24. Location of the four ore lenses A/B, C and D modelled.....	45
Figure 25. Wireframe A/B from above and section line (black dashed line; see next figure). 47	
Figure 26. Wireframe A/B in section (location of section line is given in Figure 26). .....	48
Figure 27. Wireframe C from above and section line (black dashed and full line; see next two figures). .....	49
Figure 28. Wireframe C in section (location of section line is given in Figure 28).....	50
Figure 29. Wireframe C in section (location of section line is given in Figure 28).....	51
Figure 30. Wireframe D from above and section line (black dashed line; see next figure). ...	52
Figure 31. Wireframe D in section (location of section line is given in Figure 30).....	53
Figure 32. Wireframe D in section (location of section line is given in figure before; dashed black line). .....	54
Figure 33. Cross plot bulk density [t/m <sup>3</sup> ] vs. Cr <sub>2</sub> O <sub>3</sub> [%] showing scatter. ....	55

## LIST OF TABLES

Table 1. Inferred resource comprising all three bodies A/B, C and D .....	11
Table 2. Summary of drill holes and trenches.....	28
Table 3. Summary of data available for drill holes and trenches (EODH: end of drill hole, SURV collar survey, DHSU: down-hole survey, DIAM: diameter of hole, GEOL: geological logging, GEOT: geotechnical logging, MINL: Logged chromite mineralisation [m], QUAL: meterage of samples assayed for element concentrations, DENS: meterage of samples determined for density); 'X' means data for complete hole or trench are available.....	29
Table 4. Core recovery and diameter in chromitiferous rock separated by interpreted bodies AB, C and D.....	35
Table 5. Lengths and percentages of the relevant rock types .....	36
Table 6. Lengths and percentages of chromitiferous rock.....	36
Table 7. Logging results for chromite mineralization.....	36
Table 8. Deviations of bulk density and Cr <sub>2</sub> O <sub>3</sub> of quarter core duplicates.....	38

<b>Table 9. Coordinates limiting the license area .....</b>	<b>39</b>
<b>Table 10. Basic statistics .....</b>	<b>42</b>
<b>Table 11. Correlation analysis of all chemical parameters .....</b>	<b>44</b>
<b>Table 12. Overview about data basis (geology, chemistry, density) for interpreted bodies ..</b>	<b>45</b>
<b>Table 13. Mineralized bodies A/B, C and D and drill holes used for wireframing .....</b>	<b>46</b>
<b>Table 14. Validation of volumes of wireframes .....</b>	<b>56</b>
<b>Table 15. Inferred resource comprising all three bodies A/B, C and D .....</b>	<b>57</b>
<b>Table 16. Inferred resource for body A/B.....</b>	<b>58</b>
<b>Table 17. Inferred resource for body C .....</b>	<b>58</b>
<b>Table 18. Inferred resource for body D .....</b>	<b>59</b>

## DISCLAIMER

This report has been prepared by DMT GmbH & Co. KG (DMT) for the exclusive use of HASAT BNO GRUP GIDA YEMEK HAYV. TEKS. INS. SAN. TIC A.S. (hereafter 'Hasat' or 'the client') on the basis of instructions, information and data supplied by the client.

No warranty or guarantee, whether expressed or implied, is made by DMT with respect to the completeness or accuracy of any aspect of this document and no party, other than the Client, is authorized to or should place any reliance whatsoever on the whole or any part or parts of the document.

DMT do not undertake or accept any responsibility or liability in any way whatsoever to any person or entity in respect of the whole or any part or parts of this document, or any errors in or omissions from it, arising from negligence or any other basis in law whatsoever. This note may contain "forward looking statements" which are based on assumptions made by DMT. There is no assurance or warranty given that any of the future results or achievements expressed or implied contained will be realized.

Likewise, DMT disclaim liability for any personal injury, property or other damage of any nature whatsoever, whether special, indirect, consequential or compensatory, directly or indirectly resulting from the publication, use or application, or reliance on this document.

## 1 EXECUTIVE SUMMARY

DMT has been commissioned by HASAT BNO GRUP GIDA YEMEK HAYV. TEKS. INS. SAN. TIC A.S. (hereafter 'Hasat' or 'the client') to prepare a mineral resource estimate based on a trenching and diamond drilling programme executed in license 200712070 in the Mugla province, Turkey. The license is held by the client. The target commodity is chromite.

The mineral project started at the end of 2016 with an initial programme of geological mapping. Based on the findings a trenching and drilling programme was planned by DMT. Resource definition work has been done following standard operating procedures (SOPs) designed and implemented on site by DMT in December 2017.

As a result of the resource definition work, 7 chromite lenses have been discovered and mapped. Results of geological logging and assays of 11 drill holes, drilled to date, have confirmed depth and continuity of chromite mineralization at 4 locations. Two showings were combined to a single wireframe named A/B, two more wireframes are named C and D. In consequence, three wireframes were modelled.

In total, densities and assay data of 112 samples have been available for this resource estimate. No block model or data interpolation has been done due to the early stage of the project. This report provides an inferred resource based on wireframes which are envelopes of chromite mineralization.

Several Cr<sub>2</sub>O<sub>3</sub> cut-off grades were applied to the resource database and corresponding average grades and densities were calculated. The portion of the assayed intervals was set in correspondence to the volume of wireframe, which again was used to calculate a bulk tonnage. Estimated tonnages range from 74 800 t with an average Cr<sub>2</sub>O<sub>3</sub> grade of 18.5 % without any application of a cut-off to 3 200 t with an average Cr<sub>2</sub>O<sub>3</sub> grade of 52.3 % at a 50 % Cr<sub>2</sub>O<sub>3</sub> cut-off grade (see Table 1).

**For this resource estimate no cut-off grade has been applied due to the early status of the project.**

In addition, some 14 % of the resource (appr. 10 000 t) might be direct shipping ore with almost 45 % Cr<sub>2</sub>O<sub>3</sub> based on a 28 % Cr<sub>2</sub>O<sub>3</sub> cut-off grade. However, a processing study must show, if any deleterious elements are acceptable.

**Table 1. Inferred resource comprising all three bodies A/B, C and D**

Cut-off Cr <sub>2</sub> O <sub>3</sub> [%]	Density [t/m <sup>3</sup> ]	Cr <sub>2</sub> O <sub>3</sub> [%]	Tonnage [t]
0	3.39	18.54	74 800
2	3.40	19.82	69 800
4	3.41	20.27	67 800
6	3.42	20.47	66 900
8	3.44	21.50	62 100
10	3.48	22.82	56 100
12	3.49	23.76	52 000
14	3.51	24.60	48 500
16	3.52	25.80	43 200
18	3.62	30.17	28 900
20	3.67	32.74	23 500
22	3.75	36.97	17 200
24	3.79	40.33	13 800
26	3.82	43.26	11 600
28	3.84	44.98	10 500
30	3.90	45.63	10 100
32	3.90	45.63	10 100
34	3.93	46.46	9 500
36	3.98	48.03	8 400
38	3.98	48.03	8 400
40	4.01	48.67	7 800
42	4.01	48.67	7 800
44	4.01	48.67	7 800
46	4.03	51.40	4 700
48	4.03	51.40	4 700
50	4.06	52.32	3 200
52	4.06	52.32	3 200

The applied interpretation concept for the wireframing should be adapted when further drilling and trenching clarifies the geological structure of chromite mineralization.

## INTRODUCTION

The mineral project started in 2016 as a grass-root exploration project. After prospective mapping found chromite lenses, trenching and drilling including assaying could verify the

geological and grade continuity to depth and the discoveries have been developed to resource status. The estimate of the inferred resource is subject of this report.

### 3 RELIANCE ON OTHER EXPERTS

This report has been prepared by DMT, for the client.


The information, conclusions, opinions, and estimates contained herein are based on:

- Information available to DMT at the time of preparation of this report,
- Assumptions, conditions, and qualifications as set forth in this report, and
- Data, reports, and other information supplied by the client and other third party sources, e.g. ARGETEST laboratory

For the purpose of this report, DMT has relied on ownership information provided by the client. DMT has not researched property title or mineral rights for the project and expresses no opinion as to the legal ownership status of the property.


### 4 PROPERTY DESCRIPTION AND LOCATION

The Mugla license area is located ca. 50 km to the E of Mugla and located between the villages Camovasi in the W, Otmanlar in the E and Sazak in the S. The license area 200712070 is covering an area of appr. 1936 ha (around 20 km<sup>2</sup>).

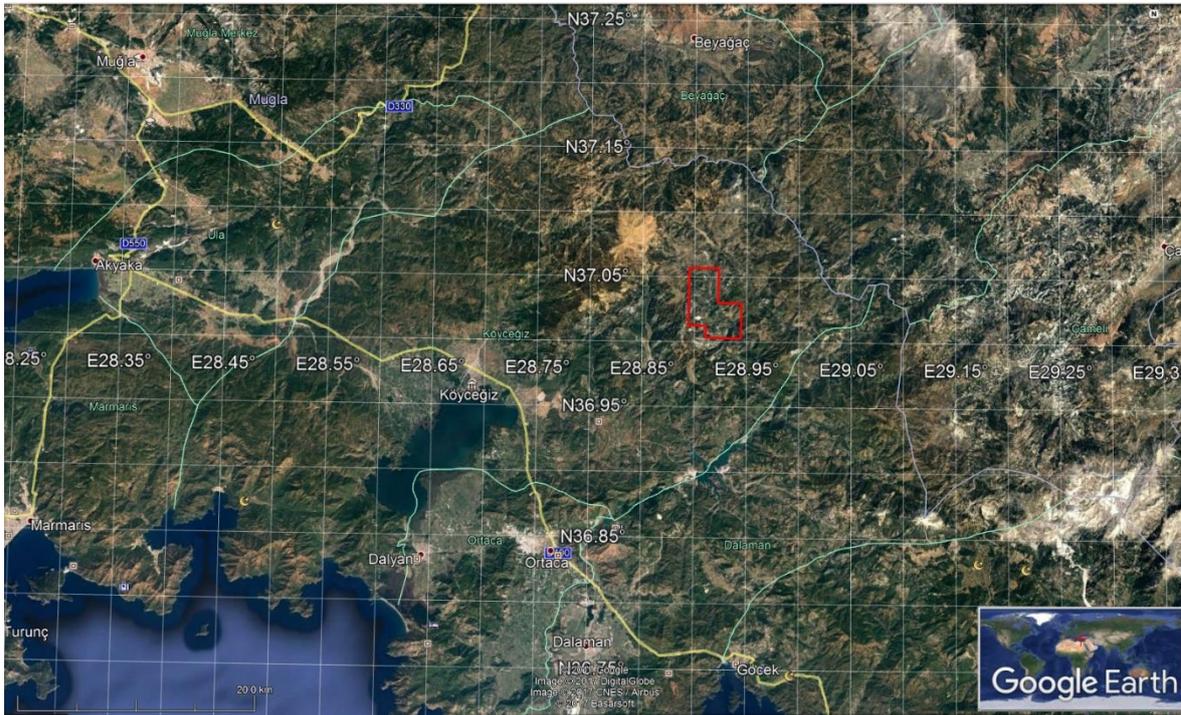

**Figure 1. Mugla license area 200712070 (red polygon) is located appr. 50 km to the West of Mugla (Source: Google Maps).**

The altitude of the license area ranges from 700 m up to 1400 m and the surface is partly very steeply incised (see Figure 2 and Figure 3).

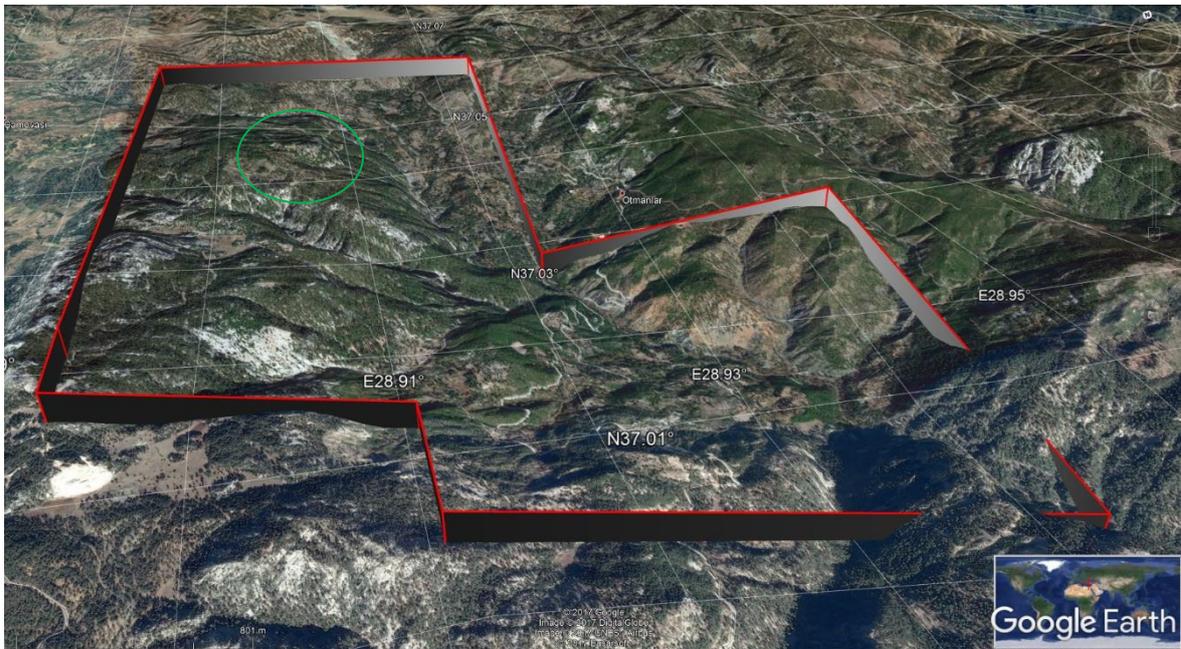


**Figure 2. The license area 200712070 (red fence) is located appr. 50 km to the E of Mugla; main area of drilling activities in green circle (Source: Google Maps).**



**Figure 3. General view of license 200712070.**

## **5 ACCESSIBILITY, CLIMATE, LOCAL RESOURCES, INFRASTRUCTURE AND PHYSIOGRAPHY**

The license area is accessible from the town Mugla within 2 hrs by car; 1 hour via D400 motorway to Mugla Fethiye Yolu and another hour via Beyobasi and Sazak on paved road through the mountains. There are major surfaced and minor roads as well as tracks made for agriculture or forestry purposes within the license area.

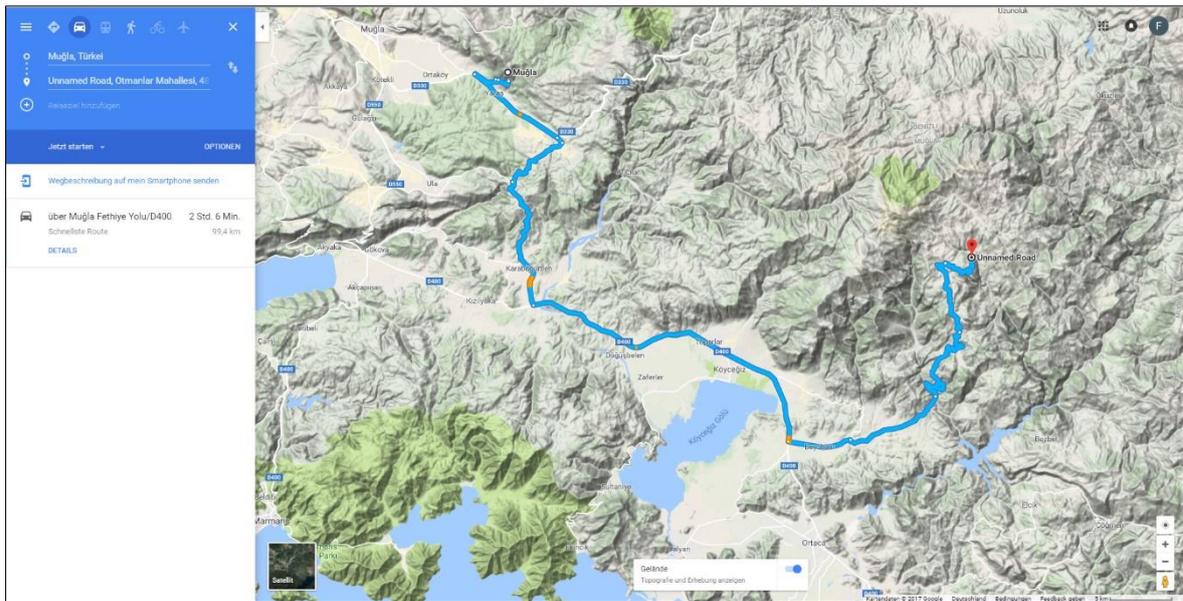

**Figure 4. Access to license from the town of Mugla (Source: Google Maps).**

Mugla is the capital of the Muğla Province, which stretches along Turkey's Aegean coast. Mugla is a relatively small city of 61,550 (2009 estimates) and has received a new boost with the foundation of Muğla University in the 1990s. Its former profile of a predominantly rural, difficult to access, isolated and underpopulated region enclosed with a rugged mountainous complex is now coming to an end. The nearest airports are Bodrum-Milas and Dalaman, each around 1.5 hrs by car (Source: <https://en.wikipedia.org/wiki/Mugla>).

Muğla has a Mediterranean climate. It is characterised by long, hot and dry summers with cool and wet winters (Source: <https://en.wikipedia.org/wiki/Mugla>).

Climate data for Muğla														[hide]
Month	Jan	Feb	Mar	Apr	May	Jun	Jul	Aug	Sep	Oct	Nov	Dec	Year	
Average high °C (°F)	10.1 (50.2)	10.9 (51.6)	14.3 (57.7)	18.6 (65.5)	24.4 (75.9)	29.8 (85.6)	33.6 (92.3)	33.6 (92.3)	29.3 (84.7)	23.3 (73.9)	16.5 (61.7)	11.4 (52.5)	21.3 (70.33)	
Average low °C (°F)	1.5 (34.7)	1.8 (35.2)	3.6 (38.5)	7.0 (44.6)	11.3 (52.3)	16.2 (61.2)	19.7 (67.5)	19.6 (67.3)	15.2 (59.4)	10.2 (50.4)	5.6 (42.1)	3.2 (37.8)	9.6 (49.25)	
Average precipitation mm (inches)	222.7 (8.768)	133.0 (5.236)	118.3 (4.657)	71.0 (2.795)	46.8 (1.843)	22.7 (0.894)	9.8 (0.386)	10.2 (0.402)	23.3 (0.917)	69.2 (2.724)	139.2 (5.48)	272.9 (10.744)	1103.1 (43.815)	
Average rainy days	14.1	13.2	10.9	9.9	7.8	3.6	1.6	1.4	2.8	6.6	9.8	14.9	96.6	
Average relative humidity (%)	76	76	72	67	61	52	45	47	50	62	73	80	63.4	
Mean monthly sunshine hours	127.1	140.0	193.1	213.0	263.5	306.0	341.0	331.7	288.0	229.4	153.0	114.7	2,696.5	

Source #1: Devlet Meteoroloji İşleri Genel Müdürlüğü [2]  
Source #2: Weatherbase [3]

**Figure 5. Climate data for Mugla.**

The climate may be challenge for open cast mining during the winter months.

## 6 HISTORY

The project started at the end of 2016 with a mapping programme identifying 7 showings of chromitiferous ultramafic rocks. No other exploration work has been done before or is reported.


Sporadic exploitation of license 200712070 takes place by farmers collecting chromitite rubble discovered during field work.

## 7 GEOLOGICAL SETTING AND MINERALIZATION

This section is sub-divided into three sub-sections describing the general situation of ophiolitic chromitites in Turkey as well as the local geology and mineralization.

### 7.1 GENERAL

Turkey has been an important producer of metallurgical-grade, high-chrome chromite. For example, Turkey was the 4th largest producer in 2005, with an estimated production of 45 Mt (Mobbs, 2007). Chromite deposits of Turkey are associated with Alpine-type peridotites that are a part of ophiolitic assemblages covering large areas, with the most important zones in northern and southern Turkey (Figure 6).

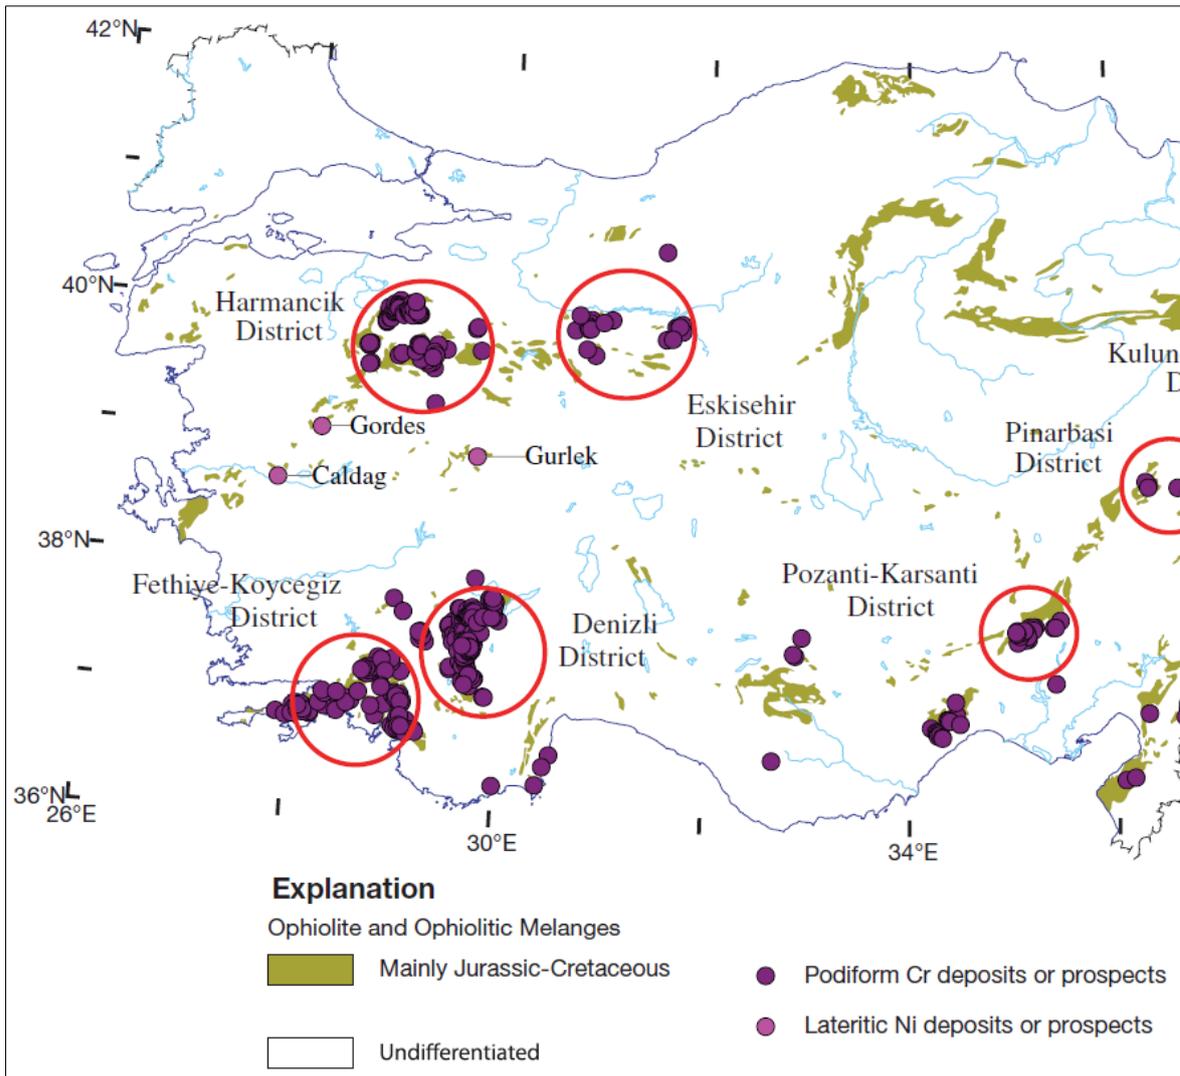

**Figure 6. Distribution of the podiform chromite districts of Turkey including lateritic nickel with emphasis on host-rock lithology (Yigit, 2009).**

Most of the ophiolitic assemblages are incomplete, except the one in Kizildag-Hatay, southern Turkey, where a complete “Trinity” sequence is found. The age of emplacement of ophiolitic rocks ranges from Jurassic to Cretaceous, but occurred mainly in the Late Cretaceous (Yigit, 2009)

Chromitite or chromitiferous lithologies are found in four stratigraphic positions of ophiolitic assemblages, which from bottom to top are as follows:


- harzburgite with enclosing dunite,
- the upper part of the tectonized harzburgite,
- dunite layers at the cumulate-tectonite contact,
- dunite layers of the cumulate sequence (MTA, 1966; Engin et al., 1987).

The podiform chromitite deposits are usually small in size, as in most other podiform chromitite deposits (rarely >1 Mt ore), with complex structural relationships and podiform, lenticular, irregular, shapeless, and/or banded type geometries (MTA, 1966; Engin et al., 1987).

## 7.2 REGIONAL

The overall metallogenic setting is ophiolitic. This metallogenic province is well known and described and further details can be read in the literature. Ophiolites are tectonically emplaced at their current position and are generally very strongly deformed.

The main source of the information for this section is Uysal (2004). The area of this study is located 17 km S of the license area (Figure 7) and describes the general geology hosting the chromite mineralization, style of mineralization and chromite composition.

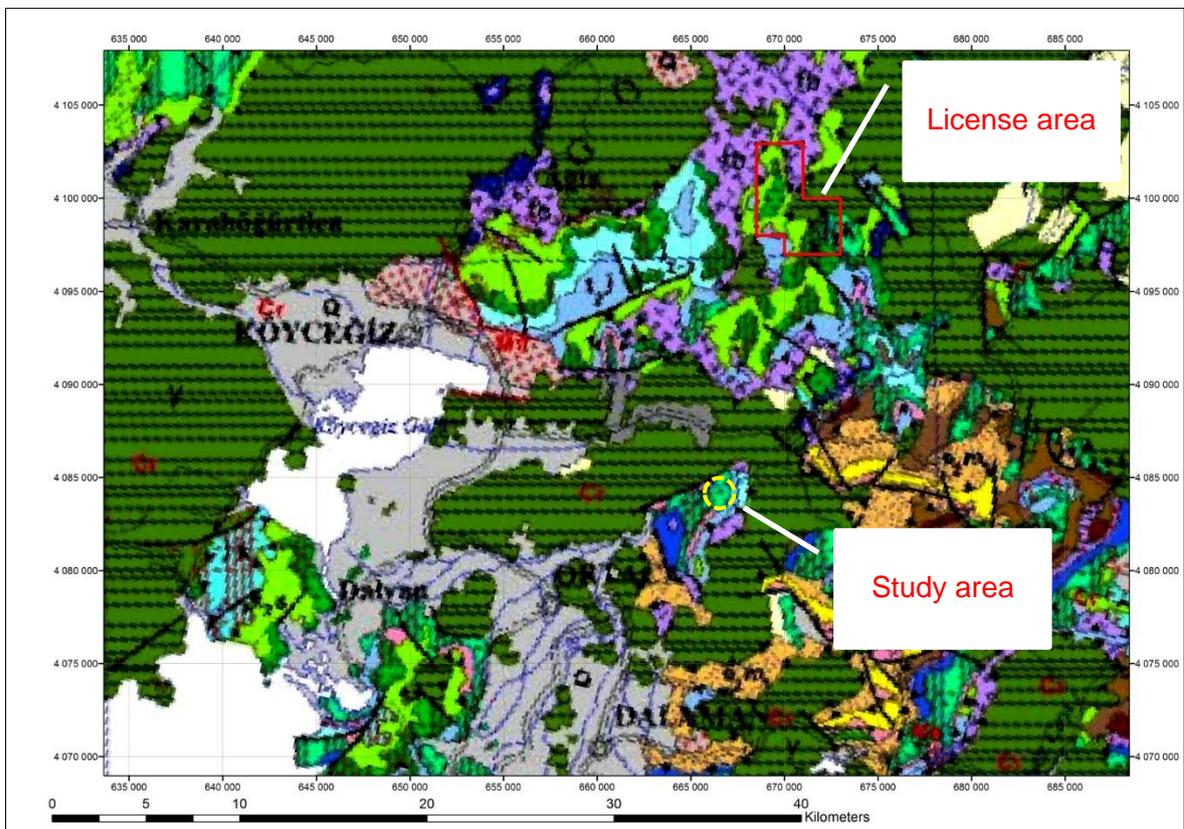

**Figure 7.** The study area is located around 17 km South of the license area in a similar geological setting as given in the license area (Source: MTA, 2002. Geological Map of Turkey, Scale 1:500 000).

### Geology:

Ultramafic rocks in the Ortaca area are interpreted to be part of the large orogenic belt extending from the Balkans through Greece, along southern Turkey into Iran (e.g., Engin,

1972; Robertson, 2002; Uysal, 2003). The ultramafic rocks, situated within the Tauride province of Southern Turkey, have been interpreted as a peridotitic complex, presumably  $88\pm 4$  to  $102\pm 4$  Ma in age (Thuizat et al., 1981). It originated in a supra subduction zone setting (e.g., Thuizat et al., 1981; Robertson, 2002; Koepke et al., 2002; Uysal, 2003; Uysal et al., 2003). Beydaglari Ootone, the Lycian nappe and the Yesilbarak nappe are essential tectonic units in the study area. Beydaglari Ootone forms a tectonic window below the Lycian nappe, and consists of Upper Paleocene–Eocene neritic limestones (Disitastepe Formation) and Lower Miocene limestones, marls and claystones (Sinekci Formation). The Yesilbarak nappe, tectonically overlying Beydaglari Ootone, is composed of Upper Luteitan-Lower Burdigalian turbiditic sandstones and shales (Elmaly Formation). The Lycian nappe is represented by the Tavas, Bodrum, Gulbahar and Marmaris ophiolites in the study area. The Tavas, Bodrum and Gulbahar nappes are represented by Carboniferous to Middle Eocene, Upper Triassic to Upper Cretaceous and Jurassic to Cretaceous rocks, respectively, while the Marmaris ophiolite consists of a Cretaceous peridotite (e.g., Senel, 1997)

The Ortaca ultramafic rocks are typically moderately to severely depleted harzburgites, as is the case for many other ophiolites around the world (Pearce et al., 1984; Roberts, 1988; Leblanc and Nicolas, 1992; Uysal, 2003). They occur as masses of highly sheared tectonites ranging in size from a few meters to several hundred meters and are intruded by dolerite dikes. The tectonites are composed of variably serpentized harzburgite and dunite, containing podiform chromitites enclosed in dunitic rocks. The harzburgitic and dunitic rocks show porphyroblastic textures with millimetre-sized porphyroclasts of brecciated olivine and, kink-banded and plastically deformed orthopyroxene. Modally less than 5 vol.% clinopyroxene is present as small crystals and exsolution lamellae in orthopyroxene.

Spinel is typically reddish-brown colored and displays corroded or elongated texture.

#### Mineralization:


The shape of the Ortaca chromitites (OC) is lens-like, the ore bodies having relatively sharp contacts with the surrounding dunites and harzburgites. In some cases, the boundaries of the ore bodies with the enclosing dunite are diffuse. Surrounding dunites and harzburgites are poor in spinel (less than 3 vol.%), which is small in size (<1mm diameter). The size of individual ore bodies and pods ranges from 0.5 to 8 m in thickness and to 50 m in length.

Chromite occurrences within the study area are mostly small bodies of massive, nodular and disseminated type chromitite. All of the deposits were mined for about 30 years since 1940 as a small source of high-Cr chromite. None of the bodies is estimated to contain more than a few thousand tons of ore. Massive chromitites are composed of subhedral chromite grains and grade into disseminated chromite in a harzburgitic and dunitic host rock. The amounts of chromite range from 50–60 vol. % in the disseminated one to 90–98 vol. % in the massive one. The interstitial matrix of the chromitites consists of olivine, serpentine minerals, accessory base metal alloys and sulphides, and arsenides. The grain size of chromite ranges from 2 to 25mm in massive ore and from 3 to 30mm in the disseminated one. Nodular ores are composed of rounded, rarely elongated aggregates of chromite in a moderately to highly serpentized matrix. The axial ratios of chromites are 2:1 in the nodular


part. The size of the nodules varies between 1 and 1.5 cm in diameter. The nodules are massive and composed of subhedral chromite grains usually <1 mm in diameter.

Mineral composition:

Chromites are usually fresh. In massive chromitites, chromite crystals display fracturing and brecciation. Podiform chromite deposits from Ortaca are characterized by chromites with Cr# [Cr/(Cr+Al)] usually from 0.73 to 0.81 and Mg# [Mg/(Mg+Fe<sup>2+</sup>)] from 0.65 to 0.71, although one chromitite sample contains chromite with Cr# of 0.61. Selected microprobe analyses of chromian spinels are presented in Table 1. Chemical zoning is very limited; locally a thin rim of ferrite-chromite along grain boundaries and cracks is developed. With exception

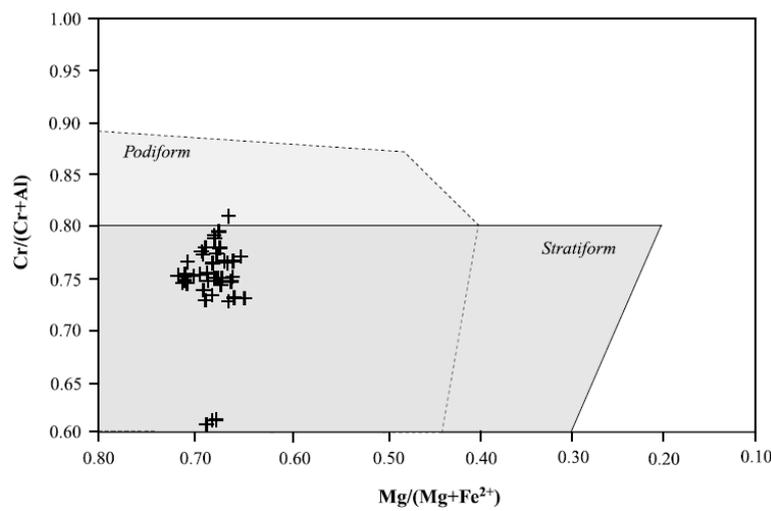

**Figure 8. Composition of chromite in the Cr/(Cr+Al) vs. Mg/(Mg+Fe<sup>2+</sup>) diagram. Fields defined for podiform (dashed line) and stratiform (solid line) chromitites according to Dick and Bullen (1984).**

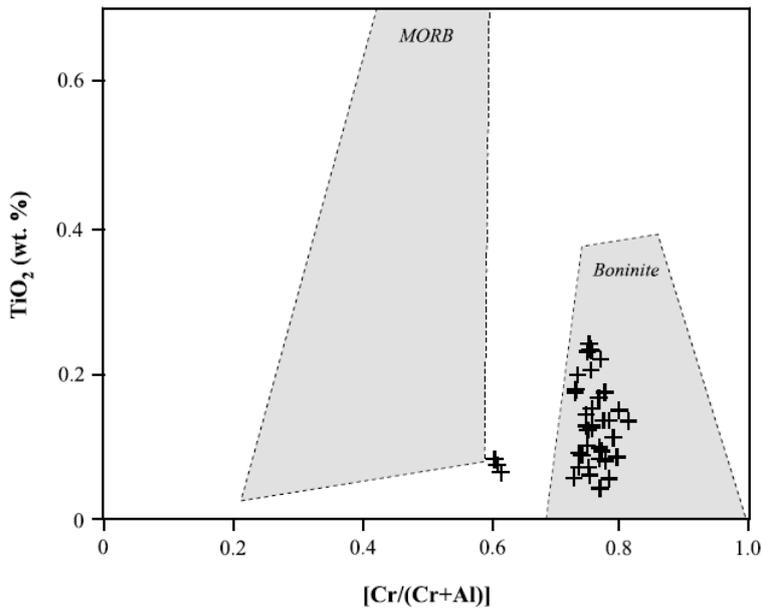

**Figure 9. TiO<sub>2</sub> vs. Cr# [Cr/(Cr+Al)] ratio of chromites of the Ortaca chromitites, showing the distinct fields for boninites and MORB (mid-ocean ridge basalts) (after Dick and Bullen, 1984; Arai, 1992).**

of one sample which is high in Al, the analysed chromites are all high in Cr. The composition of chromites from the OC deposits vary within the following ranges:

Cr<sub>2</sub>O<sub>3</sub>: 48.90–61.42 wt.%,

Al<sub>2</sub>O<sub>3</sub>: 9.79–21.33 wt.%,

MgO: 13.45–15.09wt.%,

FeO: 10.74–13.60 wt.%,

Fe<sub>2</sub>O<sub>3</sub>: 1.81–4.44 wt.%.

Minor amounts of TiO<sub>2</sub> (0.04–0.24 wt.%) and MnO (0.15–0.28 wt.%) were also detected. The diagram Mg/(Mg+Fe<sup>2+</sup>) vs. Cr/(Cr+Al) indicates that almost all samples plot within the overlapping field for podiform and stratiform type (Figure 8). On a diagram of Cr/(Cr+Al) vs. TiO<sub>2</sub>, most chromitites plot in the boninitic field; only three analyses of one chromitite sample plot near the MORB field as defined by Dick and Bullen (1984) and Arai (1992) (Figure 9).

The conversion factor from Cr to Cr<sub>2</sub>O<sub>3</sub> is 1.462.

### 7.3 PROPERTY

This section is largely based on the site visit by Dr. Bernd Teigler (QP) in 2016, during which the following salient observations have been made:

- Typical rock types of an ultramafic sequence in an ophiolite complex are widespread.
- All lithologies are severely tectonised.
- Serpentinisation of the ultramafic units is common. The degree varies.
- Clearly identified lithologies are serpentinite after dunite and harzburgite, chromitite and gabbro.
- Sedimentary rocks and massive chromitite have been observed as scree only.

Two types of chromite mineralisation have been observed. As clarification the present writer uses the term massive chromitite for rocks with more than 50 % chromite indicating a  $\text{Cr}_2\text{O}_3$ -content of more than 25 %. Rocks with less than 50 % chromite are called chromitiferous ultramafic (see Figure 10). If chromite is present as an accessory phase the term “disseminated” is used.

Both types of mineralization appear to be of economic interest. Non-systematic rock grab sampling has indicated  $\text{Cr}_2\text{O}_3$ -contents of up to 46 %. It appears that the massive chromitite is only weakly to moderately magnetic in contrast to the heavily serpentinised ultramafic hosts.

A second location with massive chromitite float, located at the NE corner of the license was also briefly visited, but did not reveal any additional information. There are further chromite showings in the license reported.



**Harzburgite, serpentinised**



**Massive chromitite**



**Chromitiferous ultramafic,  
serpentinised**

**Figure 10. Lithologies observed. Top right: contact between ultramafic and gabbroic rocks. Top left: contact between ultramafic and strongly altered lithology.**

## 8 EXPLORATION

Site visit showed that the license indicates encouraging evidence to continue with exploration. Showings with economically interesting values have already been discovered and sporadic exploitation has occurred. Based on the field visit and the work done by other workers a decision to invest in more exploration was recommended.


Following-up geological mapping of parts of license 200712070 Otmanlar (Mugla) was successfully performed by Hasat's staff and several chromite mineralized prospects identified. A large proportion of the license area has not yet been mapped.

Further geological details were recognised during the geological mapping by Hasat's staff during November and December 2016. Mapping along selected lines and of two additional road cuts was done during this period of time. Focus was on already identified chromite mineralization and its geological/structural setting. Along the lines waypoints or points of observations were marked and all relevant data recorded together with structural measurements. A total of 293 points of observations are available along the lines A – R and road cuts 1 and 2.


All data have been transferred into excel spreadsheets, so that the use in a GIS software was possible, which assisted the planning of the next phase of trenching and drilling.

Geological mapping covered sedimentary as well as igneous lithologies. The latter are the hosts to the chromite mineralization. Lime- and dolostones were observed to cover major proportions of the license area and appear to be associated mostly with reversed faulted sections in the S and N part of the license. They are underlain by ophiolitic lithologies, viz. massive ultramafic and mafic rocks (dunite, clinopyroxenite, chromitite and gabbro). All primary ultramafic lithologies are severely serpentinised and primary textures are very often completely overprinted by serpentinisation thus hampering unequivocal identification.

Figure 11 shows the results of the geological mapping, while Figure 12 displays the geological legend. Hasat's staff have observed eight locations, which may indicate chromite mineralization, volume, tonnage or grade cannot be gauged from mapping results.

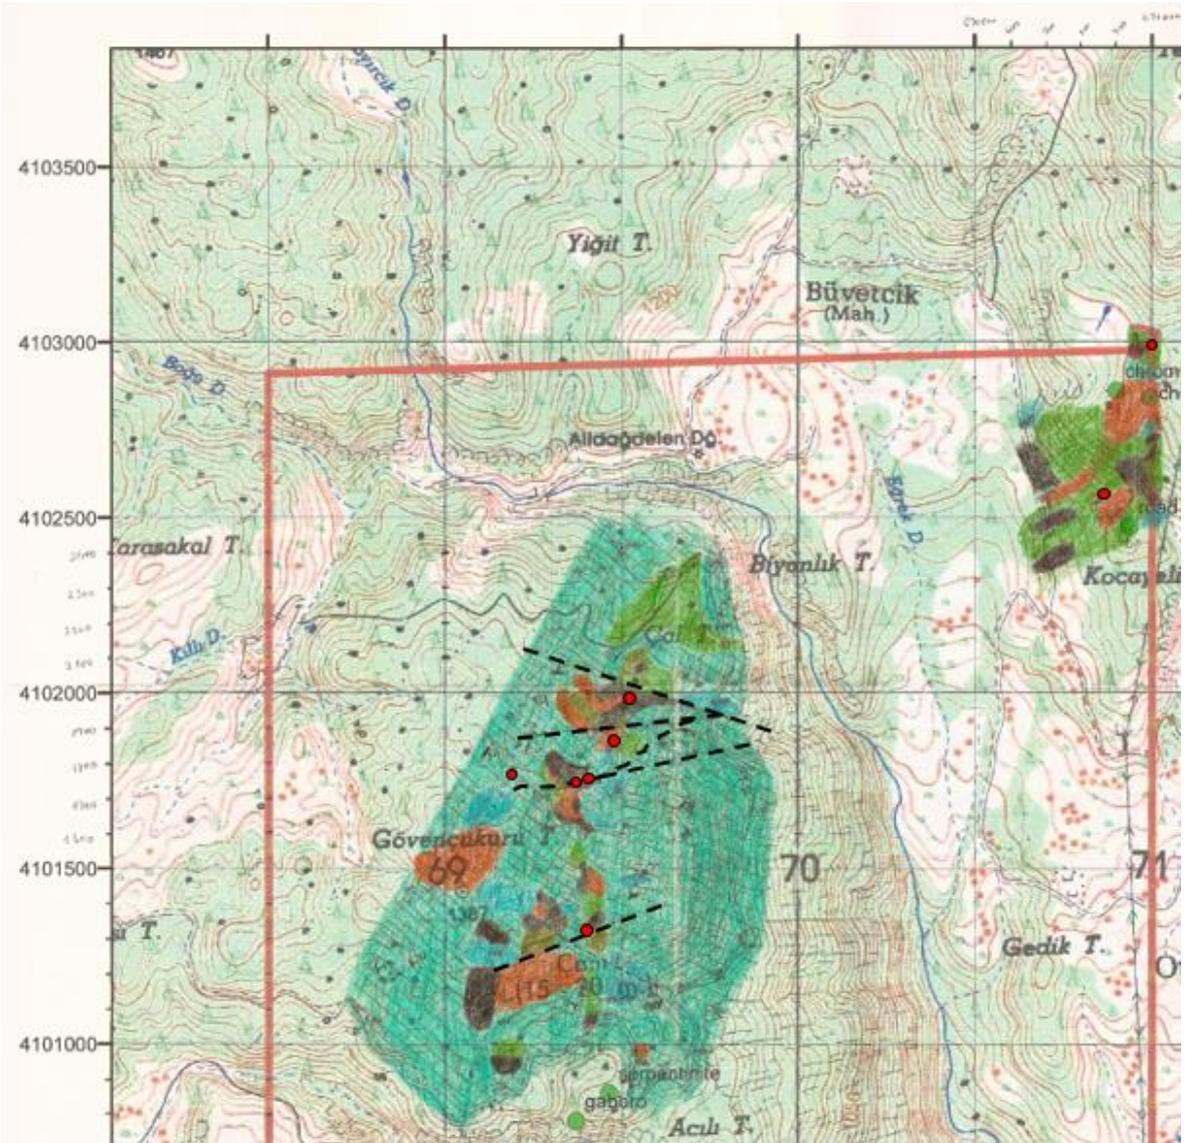

**Figure 11: Results of the geological mapping (chromite - red dots and probable faults - dashed lines).**

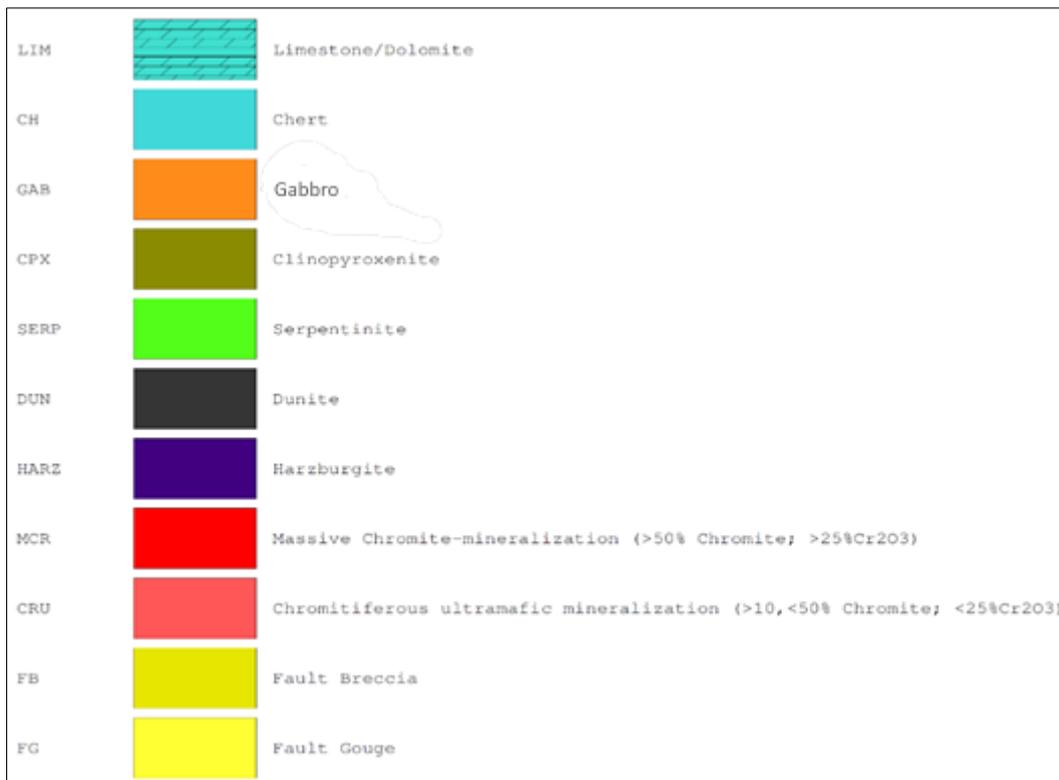

**Figure 12: Lithological legend.**

Based on these results, DMT recommended a full interpretation and planning of a trenching/drilling programme to locate the chromite mineralization in situ and to test any depth continuation of mineralization with the main objective to develop a resource.

The results of geological logging of 8 drill holes, drilled until end of 2017, confirmed depth continuity of chromite mineralization at 4 locations. Preliminary wireframes had been modelled resulting in appr. **58 000 t** of chromitiferous rock. Results of 17 pilot samples looked promising averaging appr. **30 % Cr<sub>2</sub>O<sub>3</sub>**. These results were reported in a TR entitled “Preliminary Estimate on the Mineral Potential and Resources for Chromite in License 200712070, Mugla Province, Turkey” prepared by DMT in December 2017.

Based on these early results, DMT planned, implemented SOPs including a sampling programme in December 2017 to achieve a representative data basis for bulk density and relevant chemical concentrations with the objective to upgrade the mineral potential to a resource.

## 9 DEPOSIT TYPES

A typical sequence of an ophiolitic sequence is shown in Figure 13.


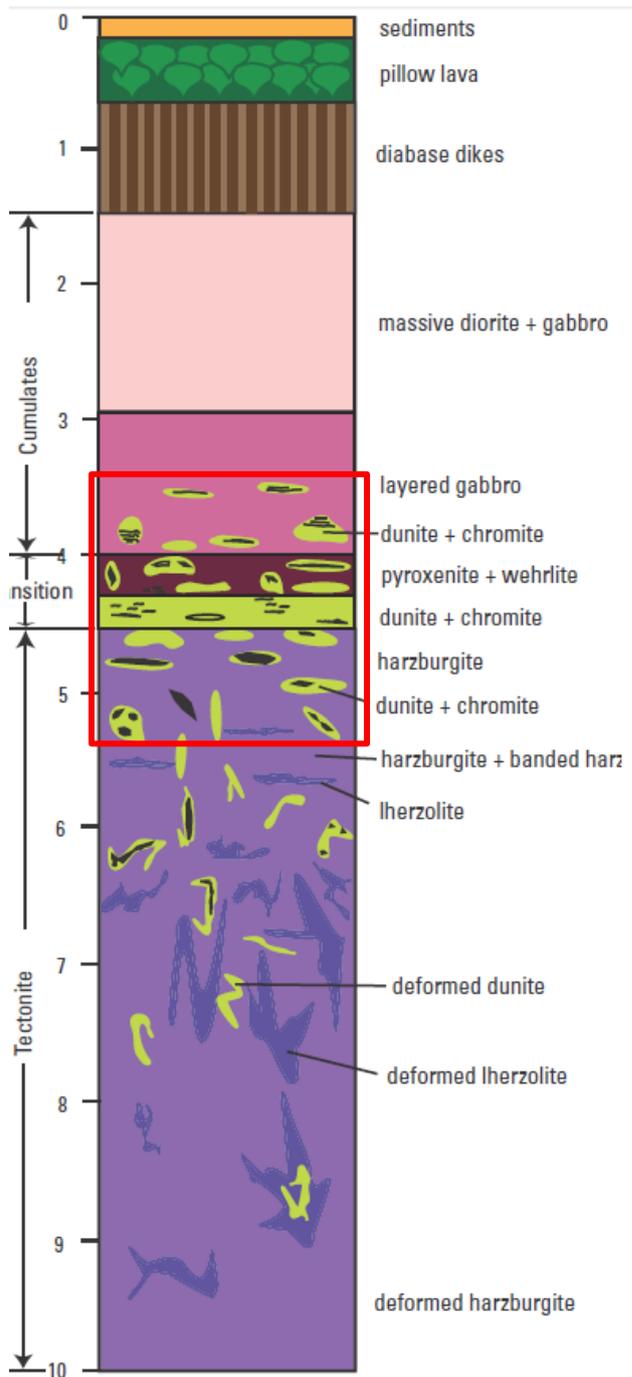


Figure 13. Typical lithological column of an ophiolite sequence (source: USGS). The red square indicates the interpreted stratigraphic position of the lithologies of interest in license 200712070.

## 10 TRENCHING AND DRILLING

Drilling after trenching was planned to test the depth continuation of 7 chromite showings identified within the mapped license area. In situ outcrops of chromitite or chromitiferous lithologies have not been found, hence trenching was supposed to be executed in order to define the general orientation of the chromite mineralization. Alternatively, scissor drilling was recommended to ensure intersections.

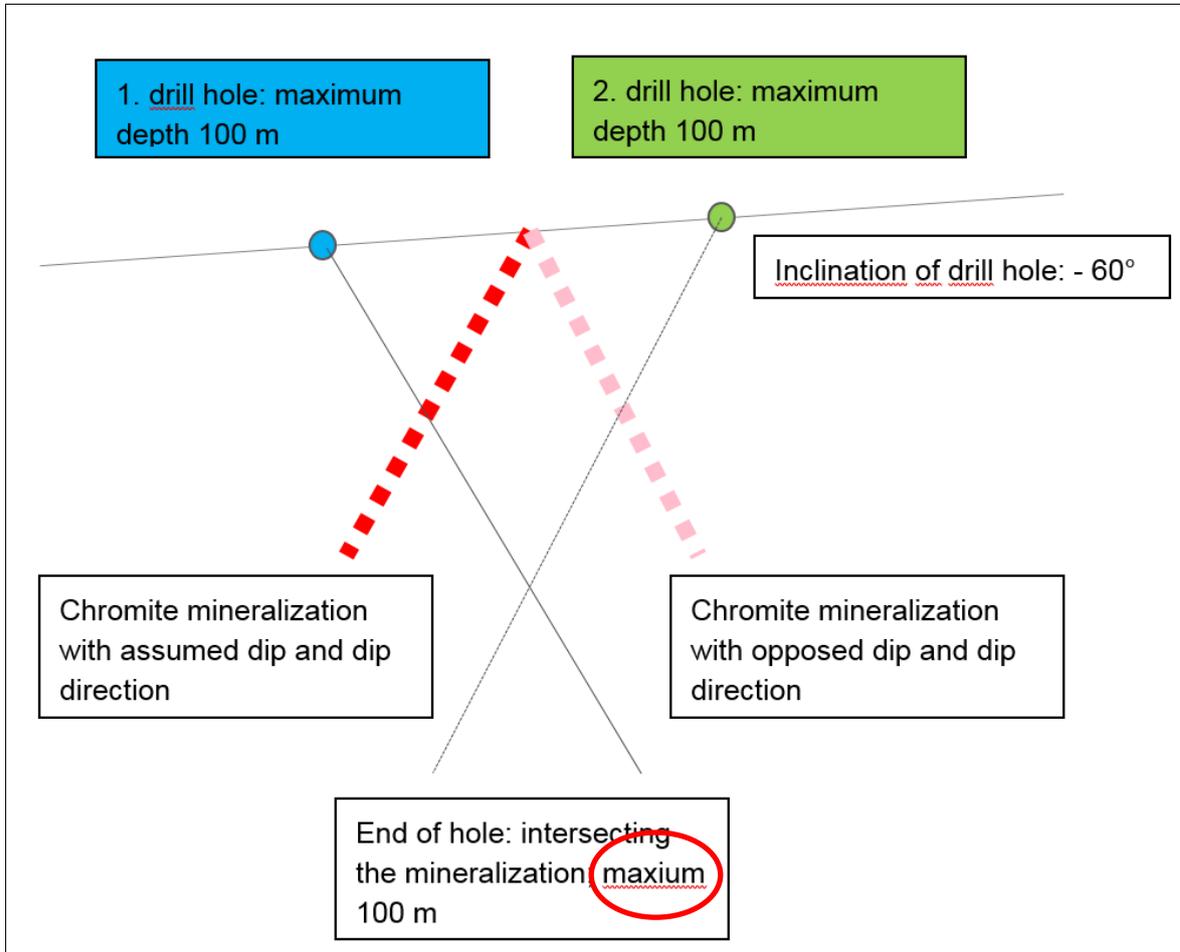

**Figure 14. Proposed scheme of exploration drilling.**

During implementation of the SOPs in December 2017, further 5 drill holes were planned to confirm the geological and grade continuity of the two main bodies AB and C.

Up to date 5 trenches (77,6 m) and 15 drill holes (764 m) have been opened and drilled, respectively. The below given table summarizes the location and orientation of the trenches and drill holes.

**Table 2. Summary of drill holes and trenches**

Hole ID	Easting	Northing	Elevation	Inclination	Azimuth	End of hole
DDH_M_001	669498.00	4102001.00	1242.00	-60.00	55.00	40.00
DDH_M_002	669533.00	4101981.00	1237.00	-60.00	285.00	100.00

DDH_M_003	669451.00	4101868.00	1252.00	-60.00	120.00	30.00
DDH_M_004	669498.00	4101854.00	1243.00	-60.00	292.00	100.00
DDH_M_005	669412.00	4101766.00	1268.00	-60.00	227.00	40.00
DDH_M_006	669378.00	4101737.00	1279.00	-60.00	47.00	40.00
DDH_M_007	669390.00	4101764.00	1272.00	-60.00	228.00	45.00
DDH_M_008	669360.00	4101732.00	1284.00	-60.00	48.00	30.00
DDH_M_009	669311.00	4101771.00	1289.00	-60.00	227.00	33.00
DDH_M_010	669300.00	4101763.00	1293.00	-60.00	31.00	28.00
DDH_M_011	669388.00	4101349.00	1341.00	-60.00	133.00	23.00
DDH_M_012	669417.00	4101313.00	1332.00	-60.00	315.00	25.00
DDH_M_015	669309.00	4101797.00	1289.00	-60.00	227.00	80.00
DDH_M_016	669288.00	4101769.00	1298.00	-60.00	52.00	80.00
DDH_M_017	669399.00	4101768.00	1275.00	-15.00	218.00	70.00
T_M_001	669507.00	4101993.00	1267.00	9.10	140.10	15.82
T_M_002	669456.00	4101862.00	1234.00	21.30	191.20	16.43
T_M_003	669405.00	4101759.00	1273.50	-6.20	232.50	31.60
T_M_004	669309.00	4101773.00	1312.00	41.50	26.30	6.00
T_M_005	669401.00	4101342.00	1330.00	0.00	50.10	7.81

Table 3 summarizes the availability on data sourced from drill holes and trenches.

**Table 3. Summary of data available for drill holes and trenches (EODH: end of drill hole, SURV collar survey, DHSU: down-hole survey, DIAM: diameter of hole, GEOL: geological logging, GEOT: geotechnical logging, MINL: Logged chromite mineralisation [m], QUAL: meterage of samples assayed for element concentrations, DENS: meterage of samples determined for density); 'X' means data for complete hole or trench are available**

DHID	EODH	SURV	DHSU	DIAM	GEOL	GEOT	MINL	QUAL	DENS
DDH_M_001	40.00	X	X	X	X	X			
DDH_M_002	100.00	X	X	X	X	X			
DDH_M_003	30.00	X	X	X	X	X			
DDH_M_004	100.00	X	X	X	X	X			
DDH_M_005	40.00	X	X	X	X	X	18.5	16.0	16.0
DDH_M_006	40.00	X	X	X	X	X	5.7	8.0	8.0
DDH_M_007	45.00	X	X	X	X	X	14.7	17.0	17.0
DDH_M_008	30.00	X	X	X	X	X	6.2	9.0	9.0
DDH_M_009	33.00	X	X	X	X	X	3.8	5.0	5.0
DDH_M_010	28.00	X	X	X	X	X	4.8	6.0	6.0
DDH_M_011	23.00	X	X	X	X	X	5.2	6.0	6.0
DDH_M_012	25.00	X	X	X	X	X	2.4	4.0	4.0
DDH_M_015	80.00	X	X	X	X	X	42.8	8.0	8.0
DDH_M_016	80.00	X	X	X	X	X	37.6	16.0	16.0

DDH_M_017	70.00	X	X	X	X	X	22.9	17.0	17.0
T_M_001	15.82	X	X						
T_M_002	16.43	X	X						
T_M_003	31.60	X	X						
T_M_004	6.00	X	X						
T_M_005	7.81	X	X						

## 11 SAMPLE PREPARATION, ANALYSES AND SECURITY

SOPs were designed and implemented in December 2017. All work of data acquisition was done or re-done following these SOPs. For details about the procedures applied see document: ‘Data Acquisition Manual – Standard Operating Procedures on the Chromite Project for License 200712070, Mugla Province, Turkey’ finalized by DMT in January 2018.

Sampling was done based on integer meter marks considering core losses. Core losses were allocated to the end of each drill run or allocated to distinct zones, when possible. The samples were taken in 1 m intervals starting two metres above visual mineralization in the hanging wall host rocks and ending two metres below visual mineralization in footwall host rocks. In each batch of 10 samples 4 QA/QC samples were inserted; two CRM samples to control overall laboratory work, one blank sample to control sample preparation (contamination) in the laboratory and one core duplicate to control sample preparation (cutting with diamond-bladed saw) in the field. Moreover, the laboratory made a second split duplicate for each 10<sup>th</sup> field sample to control sample preparation (sample reduction) in the laboratory.

In total, 156 samples (112 samples from drill holes) were dispatched to laboratory ARGETEST, which is certified to ISO Quality Management System ISO 9001: 2008. All samples were sent as half core, despite the core duplicates (quarter core). All samples were measured for density using laboratory code SGR-02 (water replacement method for complete unbroken half-core sample; see Figure 15). Thereafter, samples were prepared using code PREP-03 and assayed using code XRF-WR01 (see Figure 16 and Figure 17)

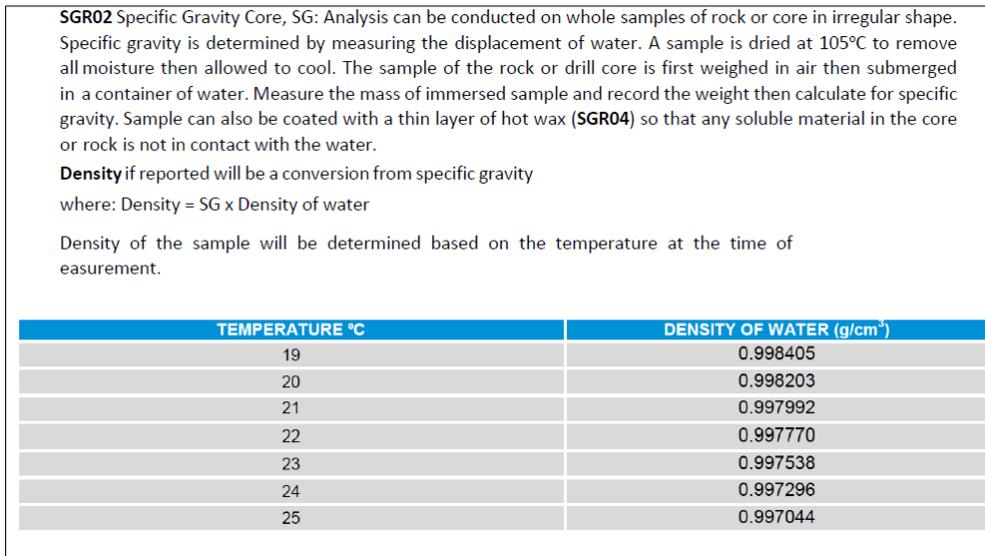


Figure 15. SGR02 - bulk density determination as described by ARGETEST.

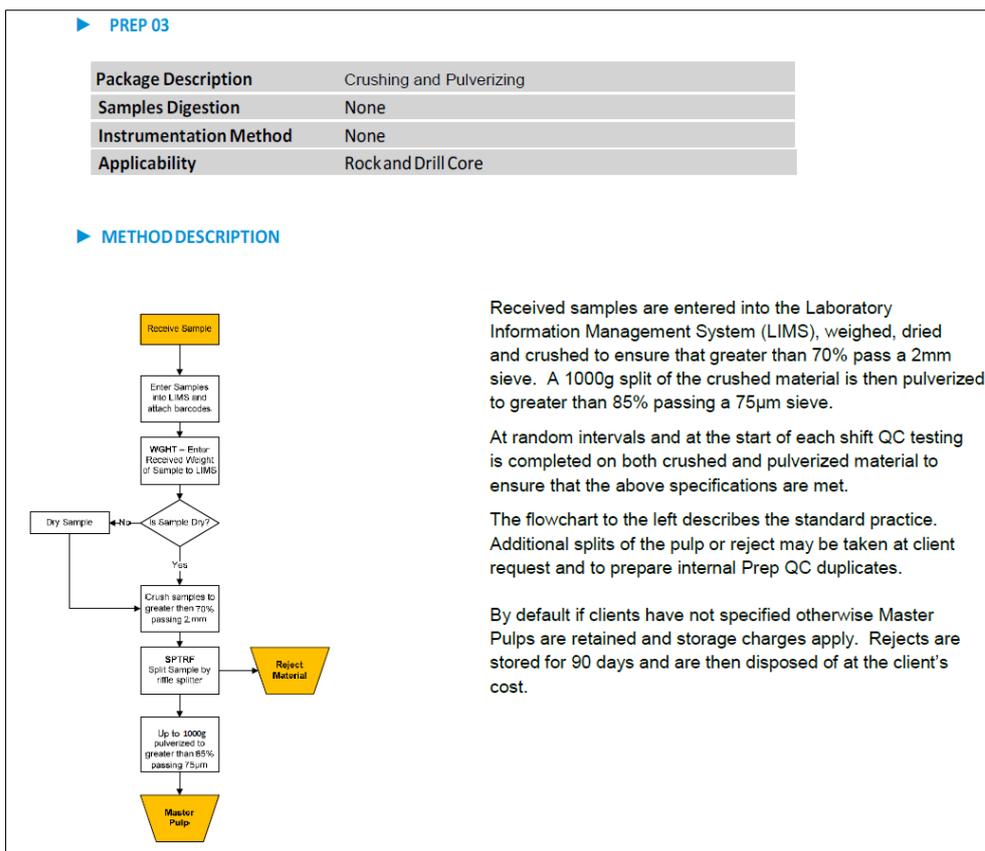


Figure 16. PREP03 - sample preparation as described by ARGETEST.

▶ XRF-WR01

Package Description	Whole Rock by XRF
Samples Digestion	Press Pellet
Instrumentation Method	X-ray Spectrometer
Applicability	Sediment, Soil, Non-mineralized Rock and Drill Core

The WR01 package is commonly used for rock characterization and is not susceptible to incomplete dissolution and matrix effects as the wet methods are. The WR01-X package reports single elements by fusion XRF.

▶ METHOD DESCRIPTION

A predetermined amount of sample is roasted to determine the loss on ignition (LOI). A second Split of sample dried at 105°C sample is then processed under high pressure. Press pellet discs are analyzed by XRF.

ELEMENT	DETECTION LIMIT	UPPER LIMIT
SiO <sub>2</sub>	0.01	100
Al <sub>2</sub> O <sub>3</sub>	0.01	60
Fe <sub>2</sub> O <sub>3</sub>	0.01	90
CaO	0.01	55
MgO	0.01	60
Na <sub>2</sub> O	0.01	50
K <sub>2</sub> O	0.01	50
MnO	0.01	90
TiO <sub>2</sub>	0.01	50
P <sub>2</sub> O <sub>5</sub>	0.01	40
Cr <sub>2</sub> O <sub>3</sub>	0.01	45
BaO	0.01	65
SO <sub>3</sub>	0.01	60
SrO	0.01	50
LOI	0.10	-

**Figure 17. XRF-WR01 - chemical analysis on pressed powder pellets as described by ARGETEST.**

PDF assay certificate and a corresponding Excel file was sent from ARGETEST directly to DMT via email.

## 12 DATA VERIFICATION

Data verification was done on several levels, which are described in detail below.

### 12.1 SITE VISITS

A visit inspecting the chromite showings in the license area has been done in 2016 by Dr. Bernd Teigler, who is a competent/qualified person registered at SACNASP.

A visit for implementation of SOPs and training of on-site personal has been done in December 2017 by Florian Lowicki who is a competent/qualified person registered at SACNASP. Florian Lowicki visited the core storage yard in the village Alibeyli, around 70 km from Izmir and around 400 km from the license area. All drill core is stored there and will be further logged, sampled and prepared before dispatch to ARGETEST in Izmir.

## 12.2 STANDARD OPERATING PROCEDURES (SOPS)

SOPs procedures set-up specifically for this project have been implemented and trained in December 2017. The SOPs include a comprehensive QA/QC management to enable DMT to control the quality and representativeness of acquired data, e.g. meter marking was controlled by photographs prior cutting, sample recovery was noted, weights of dispatched and received sample were recorded and QA/QC sample sets were included in each batch of 10<sup>th</sup> samples (see details in chapter: ‘Sample Preparation, Analyses and Security’)

The client has contracted Aktif Yerbilimleri A.S. (AY) to manage the exploration programme in the Mugla license. This company is specialized on several ground activities for mining and civil infrastructure. AY is doing all survey work and all work related to geological logging, sampling, sample preparation and sample dispatch.

All laboratory work is done by ARGETEST, a laboratory certified to ISO Quality Management System (ALS: ISO 9001:2008). ARGETEST provided results of bulk density and assay data for each sample submitted.

## 12.3 AVAILABILITY OF DATA

Up to date, 5 trenches (77,6 m) and 15 drill holes (764 m) have been cut and drilled, respectively. The following data sets are available for 15 drill holes (for details see Table 3 in chapter: ‘Trenching and Drilling’):

- Collar location and orientation
- Hole deviation
- Drill diameter
- Core recovery
- RQD: geotechnical rock quality data
- Geological logs distinguishing host rocks and several grades of chromite mineralization
- Sample list comprising samples from drill holes including ‘from’ and ‘to’ intervals of 1 m marking, sample recovery, portion and degree of chromite mineralisation and QA/QC samples plus information about name of laboratory and methods to be applied for density determination on unbroken half-core, sample preparation and chemical analysis.
- Assay certificates as PDF signed by ARGETEST and corresponding Excel file including the bulk density in [t/m<sup>3</sup>] and following chemical parameters in [%]: Al<sub>2</sub>O<sub>3</sub>, BaO, **CaO**, **Cr<sub>2</sub>O<sub>3</sub>**, Fe<sub>2</sub>O<sub>3</sub>, K<sub>2</sub>O, LOI, MgO, MnO, Na<sub>2</sub>O, P<sub>2</sub>O<sub>5</sub>, **SiO<sub>2</sub>**, SO<sub>3</sub>, SrO, TiO<sub>2</sub>
- Coordinates and elevations of drill hole collars were provided by the client to DMT in map datum UTM ED50 Zone 35 Northern Hemisphere.

License coordinates were provided by the client to DMT in map datum UTM ED50 Zone 35 Northern Hemisphere. The license certificate was provided to DMT as well.

A detailed geological map of the license area scaled to 1:25 000 has been provided by the client to DMT. This map was given in map datum UTM ED50 Zone 35 Northern Hemisphere.

A topographical map scaled to 1:25 000 was provided by the client to DMT in map datum UTM ED50 Zone 35 Northern Hemisphere.

## 12.4 DATA PREPARATION AND MANAGEMENT

All data of drilling and trenching has been compiled to a Relational Database Management Software (RDBMS), Microsoft Access, in order to be checked for consistency and errors. Thereafter data has been transferred to the modelling software Geovia Surpac to visualize the drill holes in a 3D environment. A digital terrain model (DTM) was also added to Surpac and visualized. Topographic, geological and geophysical maps have been draped onto the DTM. Available collar locations were validated against the DTM, surface topographic features, geology mapped and license boundaries.

All these data are the underlying basis for the geological interpretation and wireframe modelling.

## 12.5 DRILLING LOCATION AND ORIENTATION

All surveying work is done by AY. All holes and trenches have been surveyed at collar position and down-the-hole, in order to identify any deviation from the planned path. A full topographic survey is planned in the near future to support planning of mining activities. Currently, a comparison of surveyed collar positions with the ASTERDEM DTM shows discrepancies of 3 meters for some of the holes.

At this early stage of work, the available DTM is appropriate. However, for a follow-up mine plan a detailed survey has to be available in order to consider morphology adequately.


## 12.6 DRILLING RECOVERY AND DIAMETER

Drilling was aimed at maximising sample recovery in order to ensure representative nature of the samples. The overall core recovery is 86 %, and 88 % for 11 holes, which intersected chromitiferous rock. The core recovery within chromitiferous rock is 76 % (165 m: 153 m NQ and 12 m HQ).

**Table 4. Core recovery and diameter in chromitiferous rock separated by interpreted bodies AB, C and D**

Interpreted Body	Diameter	Metres in chromitiferous rock	Core recovery [%]
AB	HQ	4.3	83
AB	NQ	63.7	71
AB	SUBTOTAL	68.0	72
C	HQ	5.6	90
C	NQ	83.4	77
C	SUBTOTAL	89.0	78
D	HQ	1.7	70
D	NQ	5.9	81
D	SUBTOTAL	7.6	78
<b>TOTAL</b>		164.6	76

The issue of increased core recoveries has been identified and will have to be considered in any follow-up drilling. However, a sample bias caused by lost core could not be observed from following cross plots of bulk density and Cr<sub>2</sub>O<sub>3</sub> vs. core recovery.

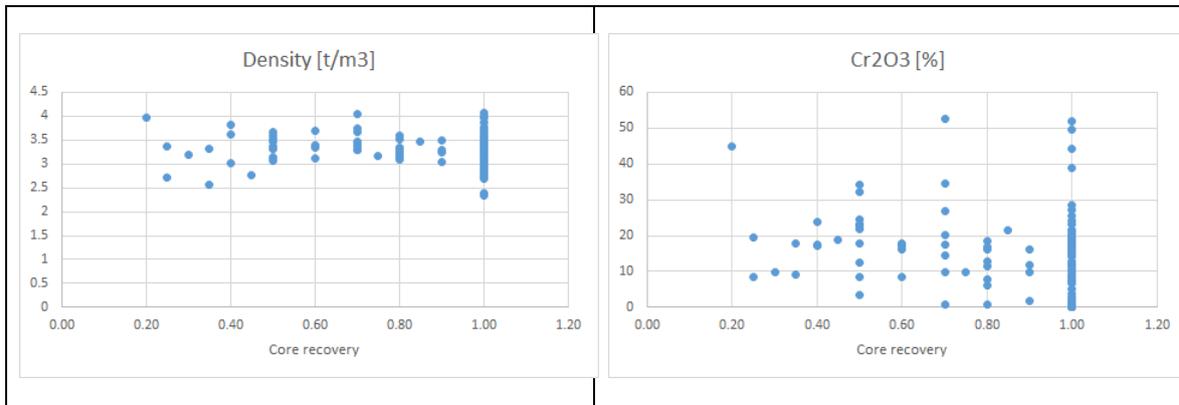

**Figure 18. Cross plots of bulk density and Cr<sub>2</sub>O<sub>3</sub> vs. core recovery.**

## 12.7 GEOLOGICAL LOGGING

Core samples have been geologically and geotechnically logged to a level of detail to support geological modelling. Logging results have been checked against drill core and core photographs. Based on these results, logging is assessed as qualitative to be used for modelling.

Table 5, Table 6 and Table 7 lists the total lengths and percentages of the relevant rock types intersected and logged.

**Table 5. Lengths and percentages of the relevant rock types**

Major rock type	Minor rock type	Meters of intersection [m]	Percentage of intersection [%]
dunite	chromitite	164.6	21.5
gabbro		3.1	0.4
gabbro	gabbro breccia	119.4	15.6
gabbro breccia	gabbro	217.4	28.5
gabbro breccia	serpentinite	15.9	2.1
lherzolite	dunite	10.2	1.3
serpentinite	gabbro breccia	212.3	27.8
soil		6.1	0.8
soil	gabbro	3.1	0.4
soil	gabbro breccia	10.9	1.4
soil	serpentinite	1.0	0.1
TOTAL		764	

**Table 6. Lengths and percentages of chromitiferous rock**

Major rock type	Minor rock type	Meters of intersection [m]	Percentage of intersection [%]
dunite	chromitite	164.6	33.3%
gabbro	gabbro breccia	42.3	8.6%
gabbro breccia	gabbro	84.1	17.0%
gabbro breccia	serpentinite	15.9	3.2%
lherzolite	dunite	10.2	2.1%
serpentinite	gabbro breccia	162.2	32.8%
soil		4.3	0.9%
soil	gabbro breccia	9.4	1.9%
soil	serpentinite	1.0	0.2%
TOTAL		494	

In total 11 of 15 drill holes intersected overall 165 m massive chromitite mineralization (Table 7).

**Table 7. Logging results for chromite mineralization**

Hole ID	From	To	Interval	Lith major	Lith minor	Degree of mineralization	Interpreted Body
DDH_M_005	21.5	40	18.5	dunite	chromitite	moderate-strong	AB
DDH_M_006	34.3	40	5.7	dunite	chromitite	moderate-strong	AB
DDH_M_007	30.3	45	14.7	dunite	chromitite	strong-massive	AB
DDH_M_008	23.8	30	6.2	dunite	chromitite	strong-massive	AB

DDH_M_009	29.2	33	3.8	dunite	chromitite	strong-massive	C
DDH_M_010	23.2	28	4.8	dunite	chromitite	strong-massive	C
DDH_M_011	17.8	23	5.2	dunite	chromitite	strong-massive	D
DDH_M_012	22.6	25	2.4	dunite	chromitite	strong-massive	D
DDH_M_015	37.2	80	42.8	dunite	chromitite	strong-massive	C
DDH_M_016	42.4	80	37.6	dunite	chromitite	strong-massive	C
DDH_M_017	36.9	59.8	22.9	dunite	chromitite	strong-massive	AB

## 12.8 SAMPLING


In total, 11 holes intersecting chromite mineralization have been representatively sampled resulting in 112 samples taken. Samples were taken on regular intervals of 1 m considering core losses. The overall sample recovery is 83 %. In total, 112 m were sampled.

In summary, 97.3 m were sampled from 164.6 m chromite-bearing rock implying that 67.3 m of chromite-bearing rock were not sampled mainly due to visually low mineralisation, especially in DDH\_M\_015 and DDH\_M\_016. Four samples could not be sampled due to heavy core loss (in DDH\_M\_005).

## 12.9 SAMPLE PREPARATION AND ANALYSIS

The sample weights received by ARGETEST are slightly higher than the sample weights dispatched from site, in average 60 g ranging from 10 g to 120 g. This variation does not affect the resource estimate and is probably due to the higher precision of the laboratory scales. Total sample weight of the 112 samples dispatched is 165 kg, weight received by ARGETEST is 171 kg.

All results of the used CRMs AMIS 0387 and AMIS 0388 fall within the recommended range. Hence, the analytical method applied is assessed as suitable to have produced reliable chemical concentrations of Cr<sub>2</sub>O<sub>3</sub>.

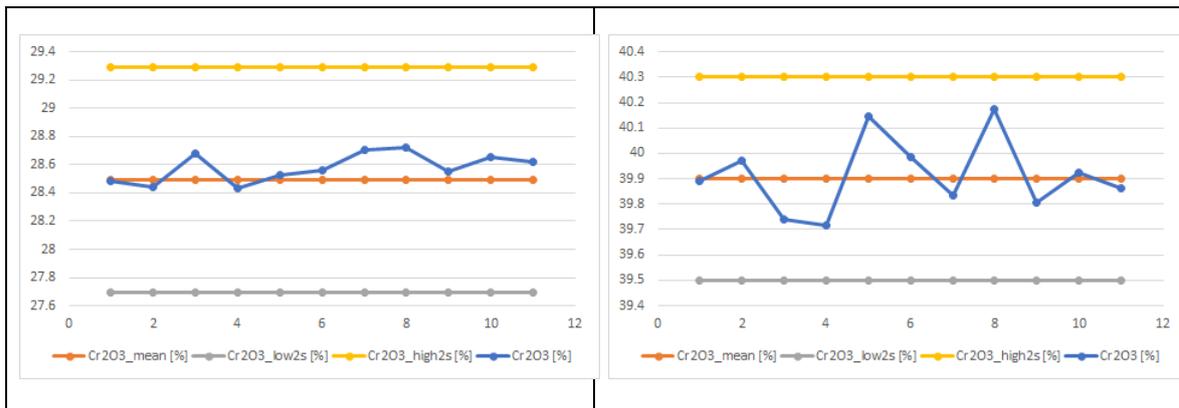

**Figure 19. Assay results for CRMs AMIS 0387 (left) and AMIS 0388 (right) for Cr<sub>2</sub>O<sub>3</sub>.**

Cr<sub>2</sub>O<sub>3</sub> concentrations of all blank samples (crushed quartz) was below the detection limit. Hence the sample preparation method is assessed to be free of contamination.


Quarter core duplicates reproduced density and Cr<sub>2</sub>O<sub>3</sub> with a deviation not exceeding 5 % for Cr<sub>2</sub>O<sub>3</sub> and 10 % for bulk density with one exception (A-0024 and A-0025). Hence, the core cutting procedure is assessed to have produced representative results. Minor deviations may also be explained by limited variations of concentrations of chromite.

**Table 8. Deviations of bulk density and Cr<sub>2</sub>O<sub>3</sub> of quarter core duplicates**

Batch ID	Duplicate Sample ID	Original Sample ID	Duplicate Density [t/m3]	Original Density [t/m3]	Density Dev [%]	Duplicate Cr2O3 [%]	Original Cr2O3 [%]	Cr2O3 Dev [%]
1	A-0011	A-0010	3.27	3.20	2.19	9.65	9.92	-2.70
2	A-0025	A-0024	3.65	3.29	10.94	22.97	26.85	-14.44
3	A-0039	A-0038	3.47	3.46	0.29	21.45	21.56	-0.48
4	A-0053	A-0052	3.37	3.41	-1.17	10.42	10.51	-0.91
5	A-0067	A-0066	3.26	3.03	7.59	17.87	17.50	2.10
6	A-0081	A-0080	3.05	2.98	2.35	6.78	7.02	-3.39
7	A-0095	A-0094	3.28	3.14	4.43	20.17	20.13	0.19
8	A-0109	A-0108	3.08	3.35	-8.06	0.06	0.06	-5.66
9	A-0123	A-0122	3.28	3.10	5.81	16.30	16.65	-2.11
10	A-0137	A-0136	3.18	3.50	-9.09	11.47	11.77	-2.62
11	A-0151	A-0150	3.58	3.60	-0.56	24.48	24.43	0.19

## 12.10 DENSITY DETERMINATION

For all samples density has been measured. A plot of densities vs. Cr<sub>2</sub>O<sub>3</sub> shows some scatter and only a weak correlation is evident. It might be that variations in chemical composition of chromite causes this scatter, but more likely other parameters are responsible, like presence of magnetite and serpentine. Tests with electron micro-probe are still outstanding. However, the measured densities are in a reasonable range and representativeness is ensured due because all core material per sample was used for density determination.

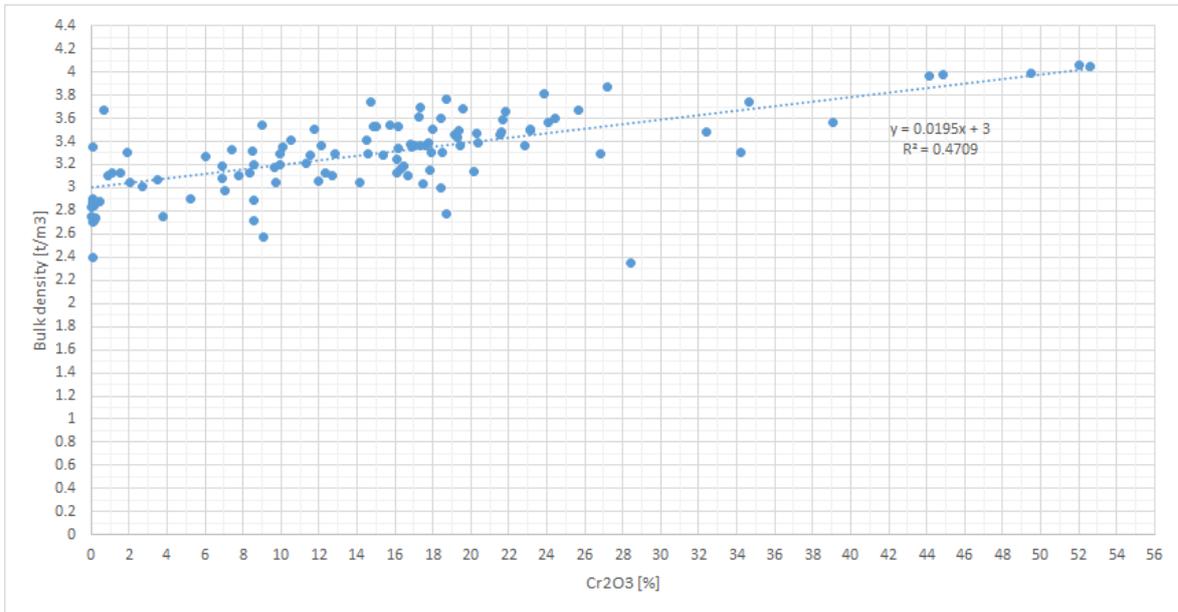

**Figure 20. Cross plot bulk density [t/m<sup>3</sup>] vs. Cr<sub>2</sub>O<sub>3</sub> [%] showing a high scatter.**

## 12.11 CONFIRMATION OF HISTORICAL DATA ACQUISITION

There is no historical data used for this estimate.

## 12.12 CONCESSION AREA

Hasat holds license 200712070 with the coordinates given in Table 9.

**Table 9. Coordinates limiting the license area**

Point ID	Easting	Northing
1	668,500	4,102,910
2	671,000	4,102,978
3	671,000	4,100,000
4	673,000	4,100,000
5	673,000	4,097,000
6	670,000	4,097,000
7	670,000	4,098,000
8	668,500	4,098,000
9	668,500	4,098,500

The license certificate was also provided to DMT. An independent validation on the license and ownership status has not been done by DMT at this stage.

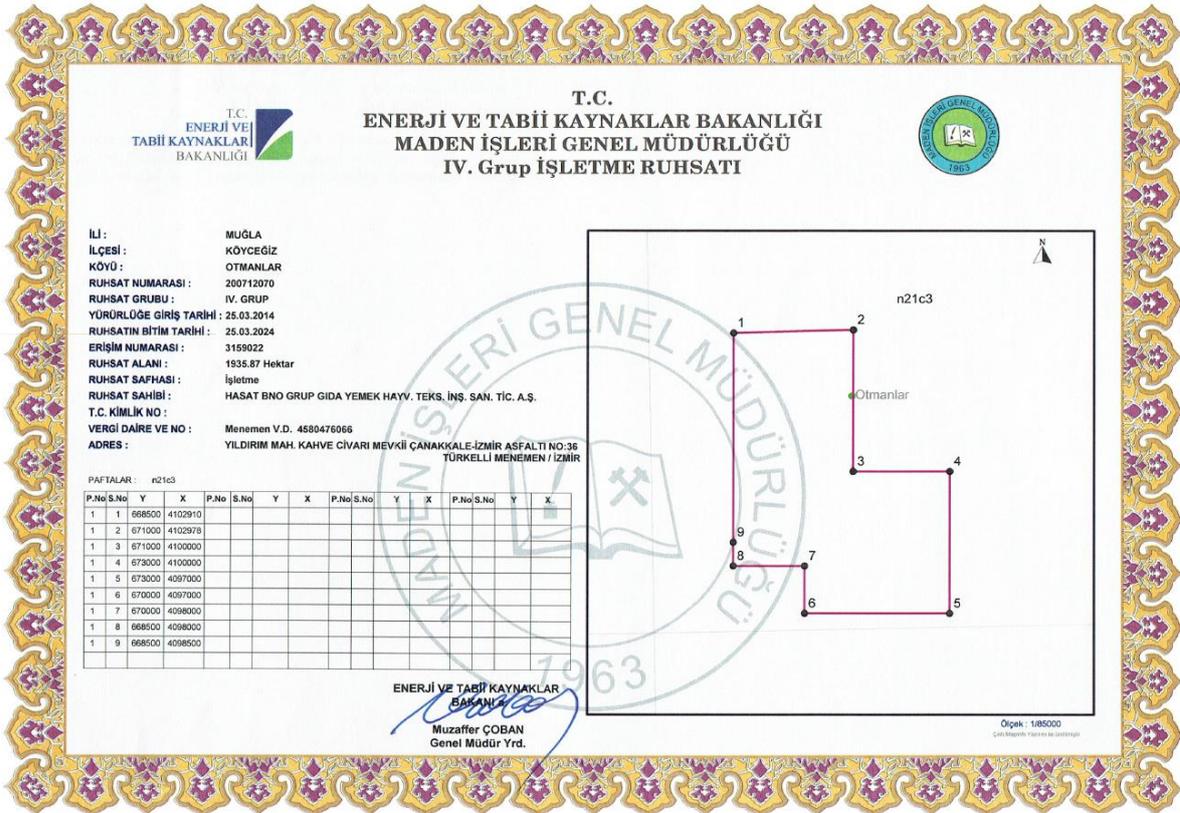


Figure 21. Certificate of license 200712070.

## 12.13 DIGITAL TERRAIN MODEL

Up to date a detailed survey of topography is not yet available. For that reason, a DTM was sourced from Global Mapper software using ASTERDEM in 1arc-second resolution in map datum UTM ED50 Zone 35 Northern Hemisphere.

## 12.14 MINED OUT AREA

Sporadic exploitation by farmers collecting massive chromitite scree distributed on the surface has occurred. It is assessed that these limited activities have no significant influence on the estimate.

## 12.15 DATA QUALITY SUMMARY

DMT assesses, that the quality and quantity of data available is sufficient to state an inferred resource. The parts where chromitiferous rock was intersected but not sampled will be

stated as upside mineral potential. This affects parts of drill holes DDH\_M\_015 and DDH\_M\_016.

## 13 MINERAL PROCESSING AND METALLURGICAL TESTING

This is an early stage project and no mineral processing and/or metallurgical test work have been done.


## 14 MINERAL RESOURCE ESTIMATES

This report provides a mineral resource estimate based on a trenching and diamond drilling programme executed in license 200712070. The basis of this resource estimate is the volume of 3 wireframes modelled based on drill holes with data of assays and density. Several  $\text{Cr}_2\text{O}_3$  cut-off grades were applied to the database. In addition, average grades and associated densities were calculated. The percentages of the remaining intervals was set in correspondence to the volume of wireframe, which again was used to calculate a bulk tonnage.

The wireframe model and estimate of this chapter are dated 22.02.2018.

### 14.1 GEOLOGICAL MODEL

The general concept, which underlies the wireframe interpretation is based on lens-shaped mineralized bodies (ellipsoid) with a lateral continuity along axis a (Figure 22: axis a\*2) not exceeding the thickness (Figure 22: axis c\*2) more than a factor of 2. For example, if two drill holes intersect chromitiferous rock in lateral distance of 20 m, the thickness was set 10 m. The continuity along axis b (longest axis) was given by the distance of chromitiferous rock at surface and drill hole contacts of chromitiferous rock in the underground.

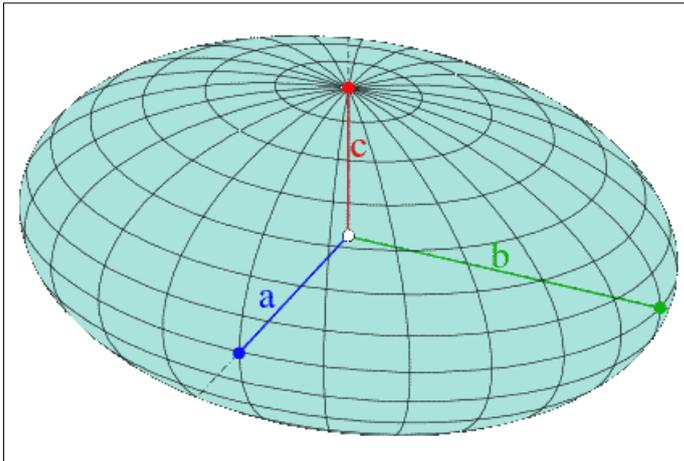

**Figure 22. Ellipsoid as geometry underlying the interpretation of chromite lenses.**

Up to date it is not known, if mineralized lenses show general orientations following strike and dip of the surrounding silicate rocks. Detailed geological logging from trenches will help to investigate the geometry in more detail and to shed light on continuity, short range modal composition of mineralization and types of surrounding rocks. Understanding of these parameters will generate higher confidence in the geological interpretation of the mineralization.


## 14.2 STATISTICAL ANALYSIS

Up to date 112 samples from drill holes are available, which are representative for the logged and interpreted mineralization. Results of basic statistics are shown in Table 10. All chemical parameters are weighted by sample length and density.

**Table 10. Basic statistics**

	Density	Al <sub>2</sub> O <sub>3</sub>	BaO	CaO	Cr <sub>2</sub> O <sub>3</sub>	Fe <sub>2</sub> O <sub>3</sub>	K <sub>2</sub> O	LOI	MgO	MnO	Na <sub>2</sub> O	P <sub>2</sub> O <sub>5</sub>	SiO <sub>2</sub>	SO <sub>3</sub>	SrO	TiO <sub>2</sub>
Mean	3.32	6.07	0.01	1.97	15.94	11.41	0.22	5.04	32.17	0.14	0.13	0.06	26.98	0.07	0.01	0.30
Std. Deviation	0.33	3.93	0.03	4.28	11.56	1.79	0.57	3.04	11.93	0.06	0.37	0.15	8.86	0.04	0.02	0.67
Minimum	2.35	0.29	0.01	0.08	0.04	4.14	0.01	0.21	2.16	0.07	-0.09	0.01	3.06	0.02	0.01	0.01
Maximum	4.06	16.96	0.24	25.38	52.64	16.93	3.48	19.48	46.22	0.36	2.18	0.91	66.92	0.33	0.11	3.86
Range	1.71	16.68	0.23	25.30	52.60	12.79	3.48	19.27	44.06	0.29	2.27	0.90	63.86	0.31	0.10	3.86
Percentiles																
10	2.88	1.89	0.01	0.12	0.67	9.77	0.01	1.81	10.91	0.10	0.01	0.01	18.33	0.04	0.01	0.03
20	3.06	2.37	0.01	0.14	6.91	10.40	0.01	3.17	17.03	0.10	0.01	0.01	21.60	0.04	0.01	0.05
30	3.14	3.56	0.01	0.16	9.75	10.76	0.01	3.68	33.08	0.11	0.01	0.01	23.63	0.05	0.01	0.07
40	3.28	4.29	0.01	0.18	12.75	11.18	0.01	4.00	35.60	0.11	0.01	0.01	24.74	0.05	0.01	0.08
50	3.34	4.94	0.01	0.22	16.09	11.32	0.01	4.22	37.19	0.12	0.01	0.01	26.60	0.06	0.01	0.09
60	3.39	6.02	0.01	0.25	17.32	11.65	0.01	4.86	38.42	0.12	0.01	0.01	28.46	0.06	0.01	0.10
70	3.49	7.47	0.01	0.42	18.98	11.94	0.01	5.53	39.29	0.13	0.01	0.01	30.30	0.07	0.01	0.12
80	3.57	10.65	0.01	1.64	21.65	12.24	0.09	6.66	41.26	0.18	0.07	0.04	32.67	0.08	0.01	0.17
90	3.74	12.02	0.01	7.35	27.88	13.39	1.00	9.36	42.87	0.22	0.49	0.16	35.82	0.09	0.04	0.67

Figure 23 shows frequency plots of bulk density and Cr<sub>2</sub>O<sub>3</sub>. It is obvious that both data sets are following more or less a normal distribution, which indicates that these data belong to a single sample population.

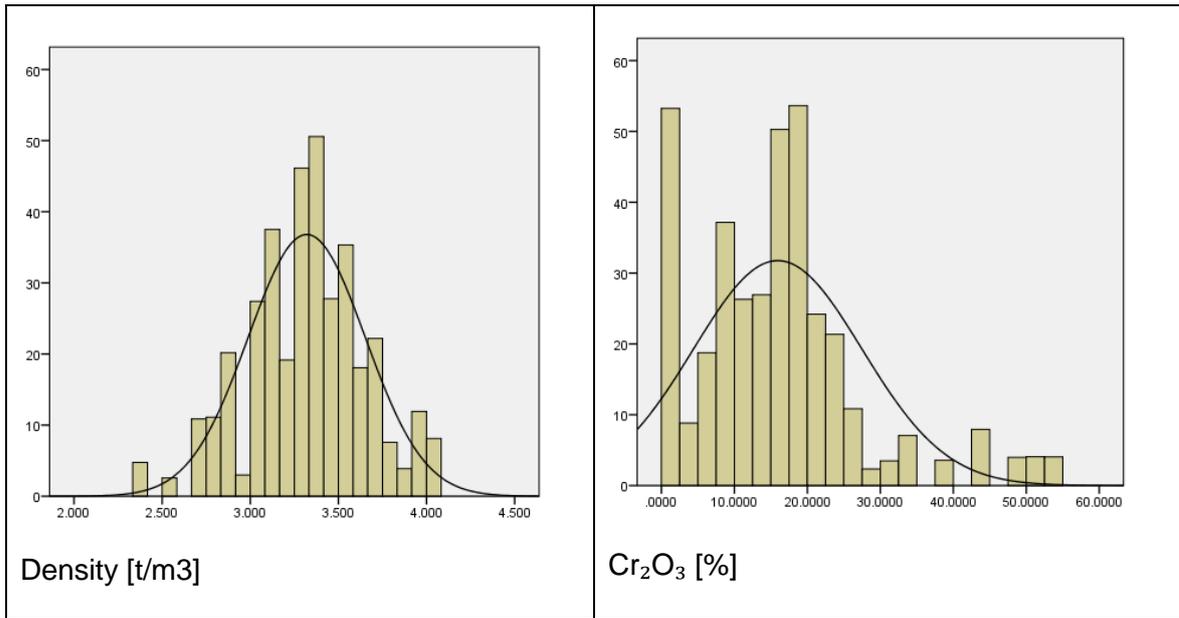

**Figure 23. Frequency plots of density and relevant chemical parameters.**

Table 11 shows a correlation analysis of bulk density and all chemical parameters assayed.


**Table 11. Correlation analysis of all chemical parameters**

		Al2O3	BaO	CaO	Cr2O3	Fe2O3	K2O	LOI	MgO	MnO	Na2O	P2O5	SiO2	SO3	SrO	TiO2
Al2O3	Pearson Correlation	1														
	Sig. (2-tailed)															
	N	112														
BaO	Pearson Correlation	.388**	1													
	Sig. (2-tailed)	0														
	N	112	112													
CaO	Pearson Correlation	.568**	.402**	1												
	Sig. (2-tailed)	0	0													
	N	112	112	112												
Cr2O3	Pearson Correlation	.252**	-.289**	-.335**	1											
	Sig. (2-tailed)	0.007	0.002	0												
	N	112	112	112	112											
Fe2O3	Pearson Correlation	.222*	-0.045	-.255**	.466**	1										
	Sig. (2-tailed)	0.019	0.636	0.007	0											
	N	112	112	112	112	112										
K2O	Pearson Correlation	.636**	.509**	.659**	-.223*	-.416**	1									
	Sig. (2-tailed)	0	0	0	0.018	0										
	N	112	112	112	112	112	112									
LOI	Pearson Correlation	.274**	.374**	.820**	-.516**	-.436**	.543**	1								
	Sig. (2-tailed)	0.003	0	0	0	0	0									
	N	112	112	112	112	112	112	112								
MgO	Pearson Correlation	-.918**	-.373**	-.763**	-0.114	0.043	-.735**	-.475**	1							
	Sig. (2-tailed)	0	0	0	0.231	0.656	0	0								
	N	112	112	112	112	112	112	112	112							
MnO	Pearson Correlation	.548**	0.076	.360**	.410**	.346**	.242*	0.053	-.588**	1						
	Sig. (2-tailed)	0	0.424	0	0	0	0.01	0.578	0							
	N	112	112	112	112	112	112	112	112	112						
Na2O	Pearson Correlation	.576**	.548**	.705**	-.297**	-0.01	.531**	.498**	-.663**	.254**	1					
	Sig. (2-tailed)	0	0	0	0.001	0.916	0	0	0	0.007						
	N	112	112	112	112	112	112	112	112	112	112					
P2O5	Pearson Correlation	.598**	.447**	.625**	-.387**	-.286**	.363**	.504**	-.582**	.300**	.703**	1				
	Sig. (2-tailed)	0	0	0	0	0.002	0	0	0	0.001	0					
	N	112	112	112	112	112	112	112	112	112	112	112				
SiO2	Pearson Correlation	-0.087	.236*	.291**	-.848**	-.651**	.403**	.355**	-0.104	-.291**	.302**	.268**	1			
	Sig. (2-tailed)	0.362	0.012	0.002	0	0	0	0	0.274	0.002	0.001	0.004				
	N	112	112	112	112	112	112	112	112	112	112	112	112			
SO3	Pearson Correlation	.460**	.588**	.668**	-.334**	-0.02	.450**	.580**	-.535**	.203*	.873**	.657**	.234*	1		
	Sig. (2-tailed)	0	0	0	0	0.832	0	0	0	0.032	0	0	0.013			
	N	112	112	112	112	112	112	112	112	112	112	112	112	112		
SrO	Pearson Correlation	.574**	.711**	.853**	-.429**	-0.024	.587**	.739**	-.658**	.251**	.763**	.805**	.296**	.784**	1	
	Sig. (2-tailed)	0	0	0	0	0.802	0	0	0	0.007	0	0	0.002	0		
	N	112	112	112	112	112	112	112	112	112	112	112	112	112	112	
TiO2	Pearson Correlation	.597**	.467**	.616**	-.370**	.314**	.337**	.492**	-.572**	.282**	.733**	.991**	.238*	.688**	.812**	1
	Sig. (2-tailed)	0	0	0	0	0.001	0	0	0	0.003	0	0	0.012	0	0	
	N	112	112	112	112	112	112	112	112	112	112	112	112	112	112	112

\*\* Correlation is significant at the 0.01 level (2-tailed).  
\* Correlation is significant at the 0.05 level (2-tailed).

### 14.3 INTERPRETATION OF MINERALIZED ZONES (DOMAINS)

For 4 chromitiferous showings continuity down-dip could be established by 11 drill holes (Table 13). Two showings were combined to a single wireframe named A/B, two more wireframes are named C and D (Figure 24). In consequence, three wireframes were modelled. There is no chromitite of chromitiferous ultramafic exposed on surface, i.e. only rubble and scree, and hence, orientation and contacts of assumed lens-shaped chromite-rich bodies are unknown at surface. A drill hole to drill hole interpretation was required.

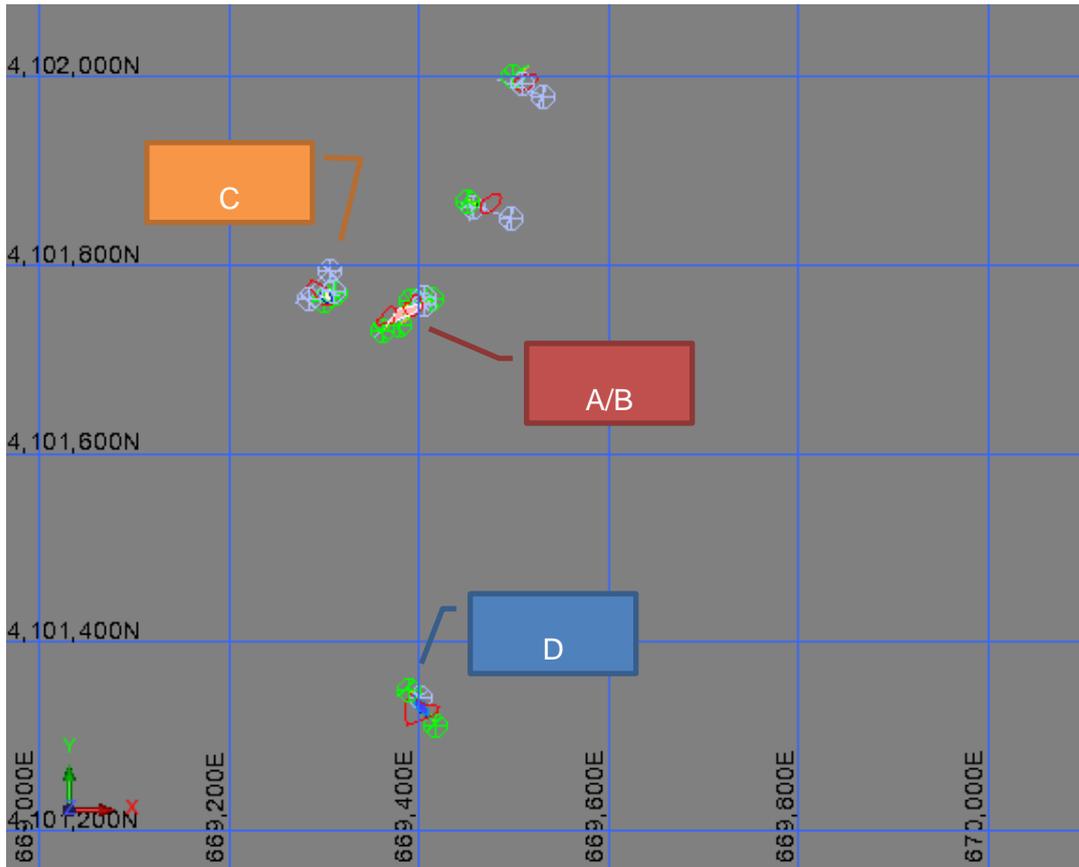

**Figure 24. Location of the four ore lenses A/B, C and D modelled.**

Following the SOPs, a minimum visual content (cut-off) of appr. 10 wt% chromite (appr. 5 wt% Cr<sub>2</sub>O<sub>3</sub>) should be within an integer meter to be taken as sample. Considering an assumed density of 4.8 t/m<sup>3</sup> for chromite 2.8t/m<sup>3</sup> for dunite, a minimum of 6 cm or 6 vol. % chromite mineralisation should be within an integer meter. That is the reason why not all material logged as chromite mineralisation was sampled.

**Table 12. Overview about data basis (geology, chemistry, density) for interpreted bodies**

Interpreted Body	Number of drill holes	Metres of logged chromite	Metres sampled and assayed intervals	Metres not sampled
AB	5	68.0	57.1	10.9
C	4	89.0	32.6	56.4
D	2	7.6	7.6	0

Wireframes were set-up connecting chromite contacts from drill hole to drill hole, when data of chemical parameters and bulk density were available. These wireframes were projected to surface and adapted not exceeding the lengths of trenches and mapped spots of chromite

rubble at surface. These wireframes resulted in 3D volume bodies. In total, 3 wireframes were modelled; A/B, C and D (Figure 24). Wireframes were modelled only in the area in-between drill holes and not extended to the untested areas beyond the drilled area in order to respect the complex geometry, which requires further investigations, e.g. trenching:

- For **wireframe A/B** chromite contacts of all 5 holes were connected to a polyhedron.
- For **wireframe C** chromite contacts of all 4 holes were connected to a polyhedron.
- For **wireframe D chromite** contacts of only two drill holes were available. Hence, the distance of the chromite contacts was used as the major axis of an ellipse, the minor axis was set to the half of the major axis.

**Table 13. Mineralized bodies A/B, C and D and drill holes used for wireframing**

Hole ID	Depth from	Depth to	Interval	Interpreted Body
DDH_M_005	21	39	18	A/B
DDH_M_006	34	40	6	A/B
DDH_M_007	30	45	15	A/B
DDH_M_008	23	30	7	A/B
DDH_M_017	42	56	14	A/B
DDH_M_009	29	33	4	C
DDH_M_010	23	28	5	C
DDH_M_015	42	50	8	C
DDH_M_016	44	57	13	C
DDH_M_011	18	23	5	D
DDH_M_012	22	25	3	D


The interpretation concept should be amended after further drilling and trenching clarifies the geological structure of chromite mineralization.

## 14.4 WIREFRAME MODEL


In total, three wireframes were modelled: A/B, C and D based on 11 drill holes, for which geological, chemical and density data were available. The following volumes were calculated.

Mineralized Body	Volume [m <sup>3</sup> ]
A/B	8 970
C	10 160
D	2 960
<b>TOTAL</b>	<b>22 090</b>


The following screenshots from Geovia's Surpac software show the wireframes from above and in 3D.

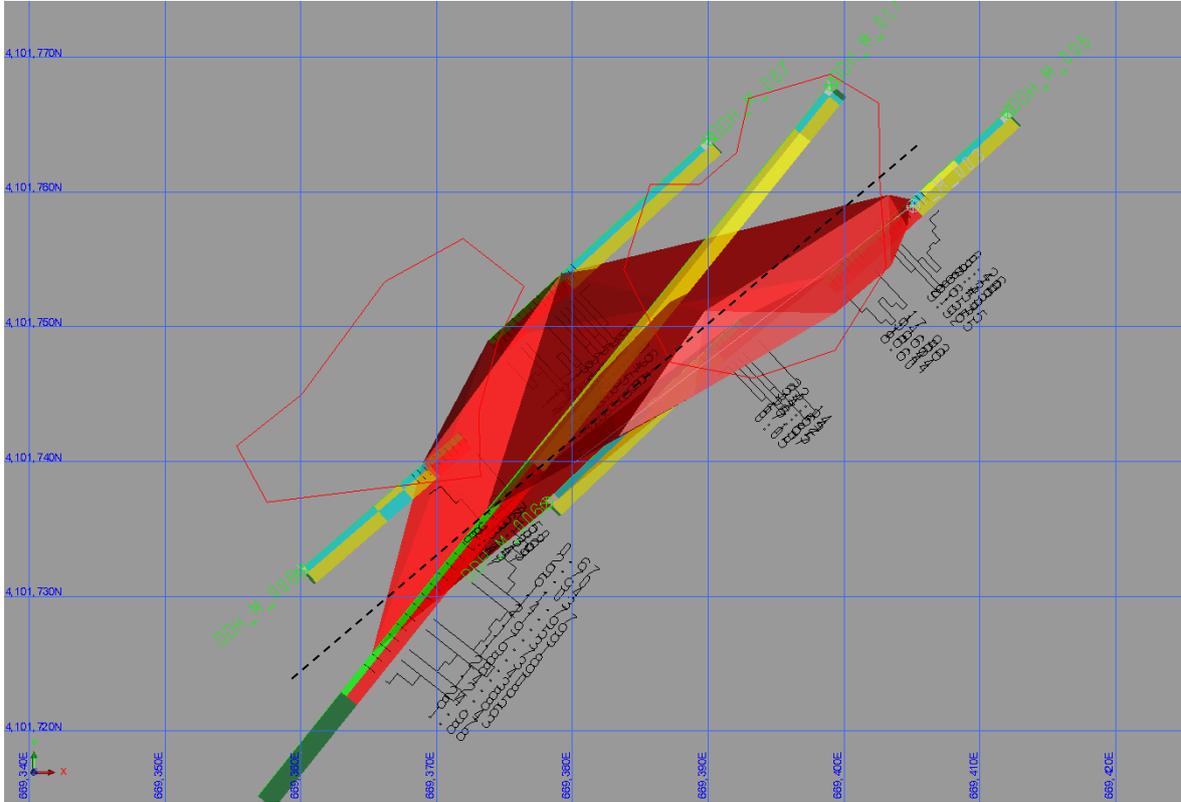


**Figure 25. Wireframe A/B from above and section line (black dashed line; see next figure).**

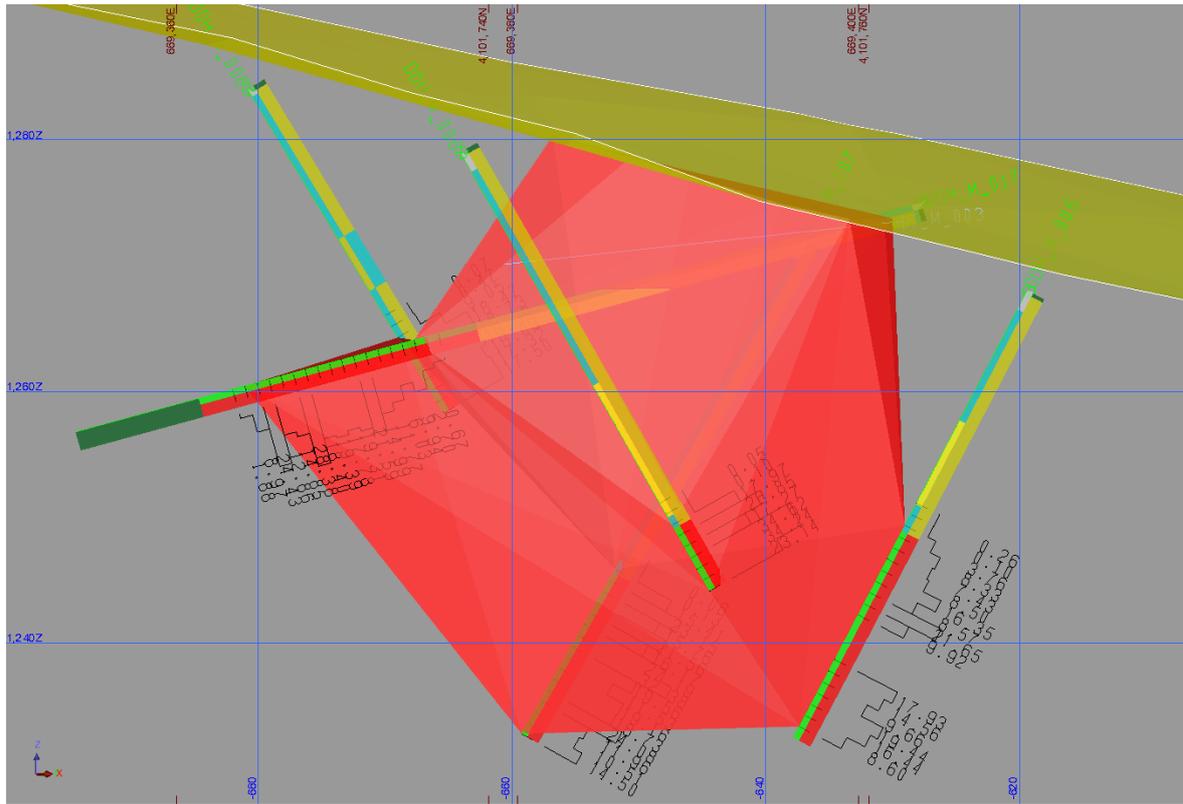

**Figure 26. Wireframe A/B in section (location of section line is given in Figure 26).**

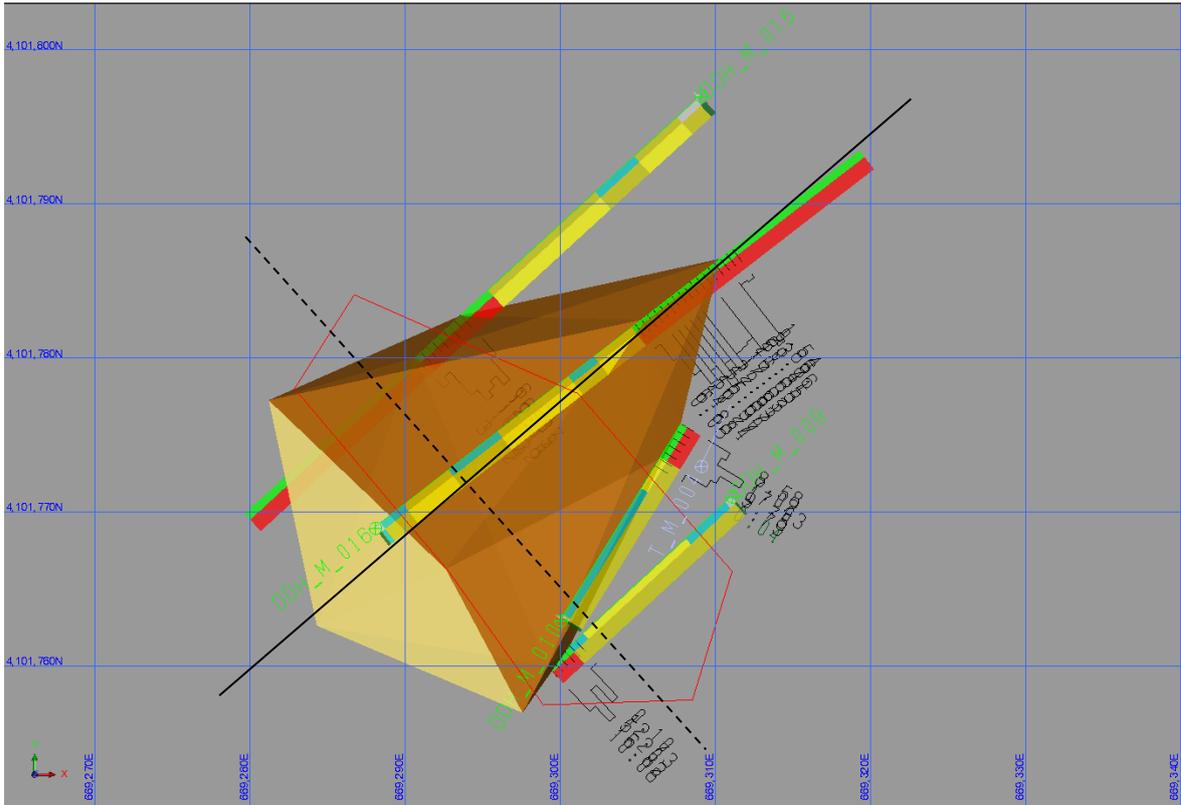

**Figure 27. Wireframe C from above and section line (black dashed and full line; see next two figures).**

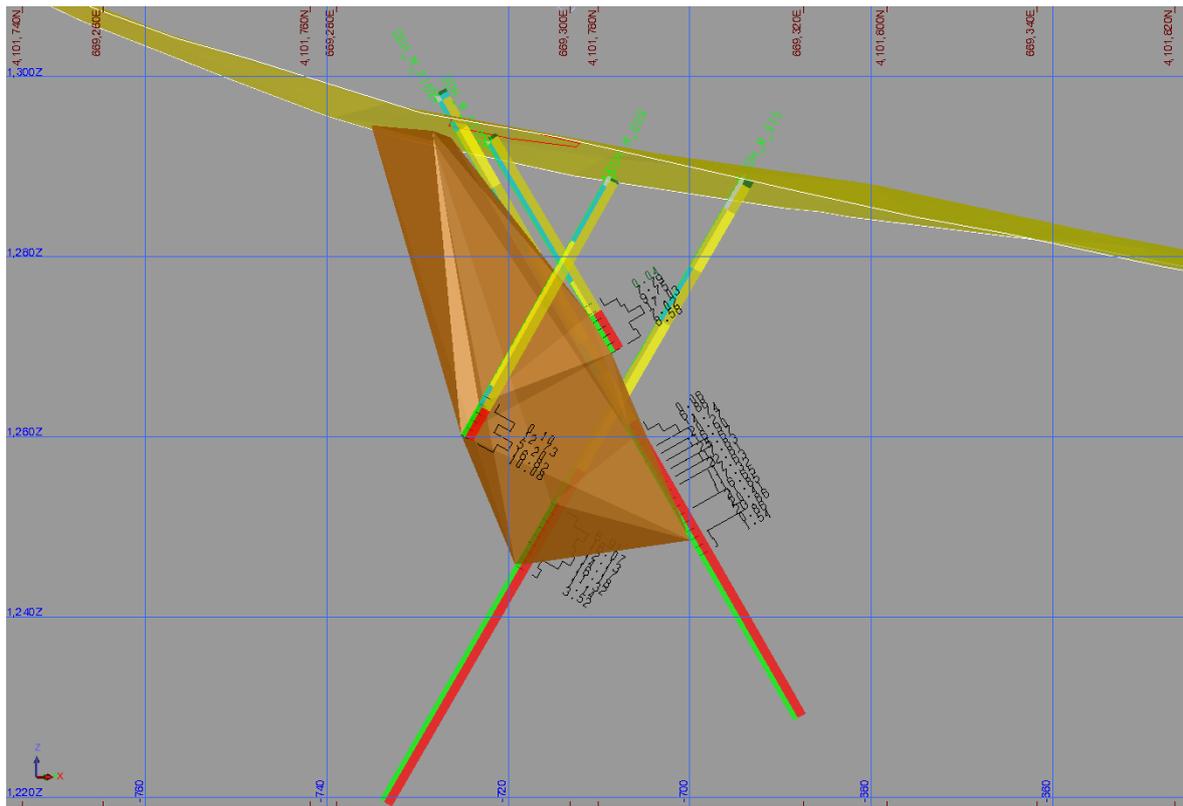

**Figure 28. Wireframe C in section (location of section line is given in Figure 28).**



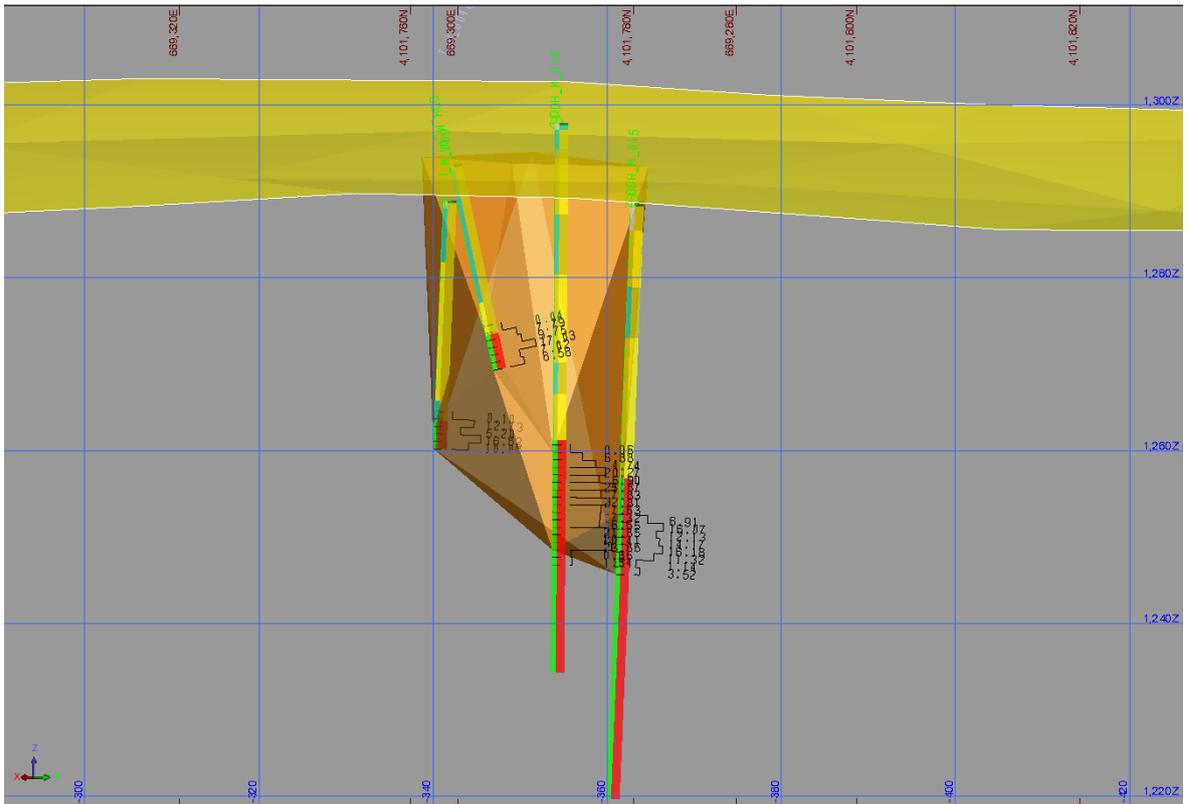


Figure 29. Wireframe C in section (location of section line is given in Figure 28).

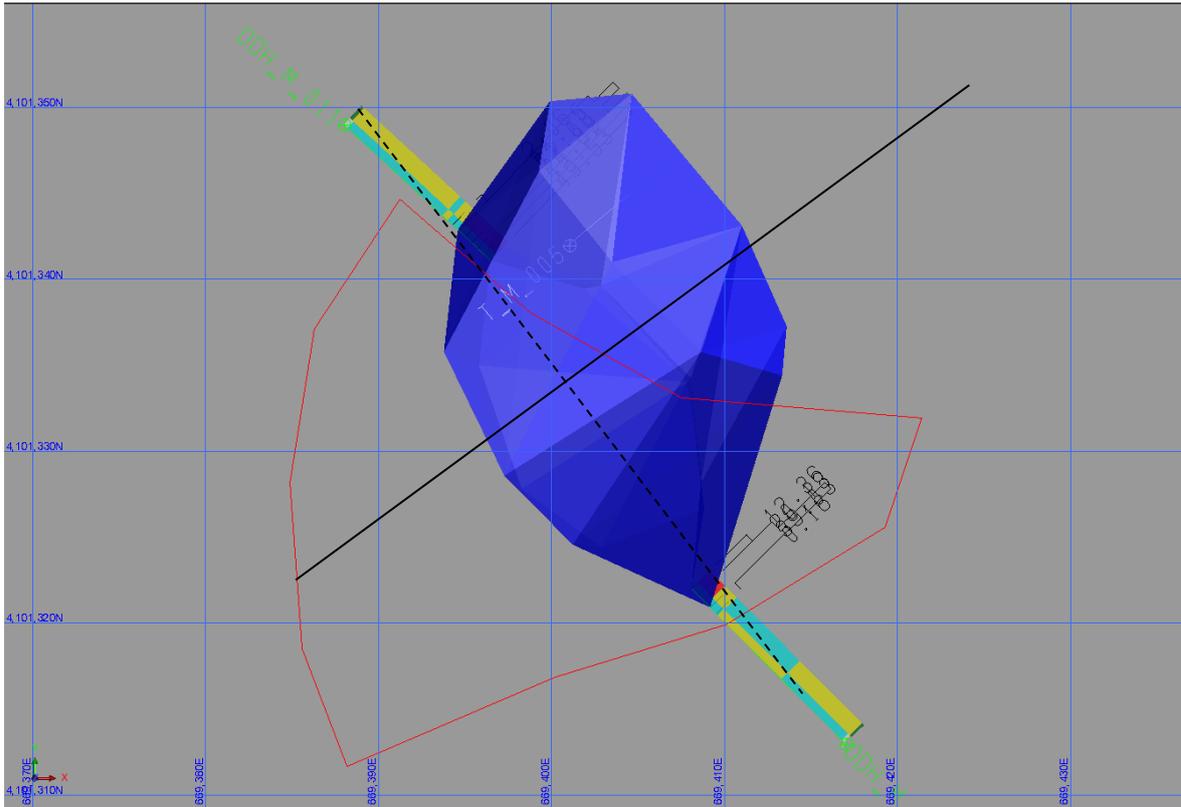


**Figure 30. Wireframe D from above and section line (black dashed line; see next figure).**

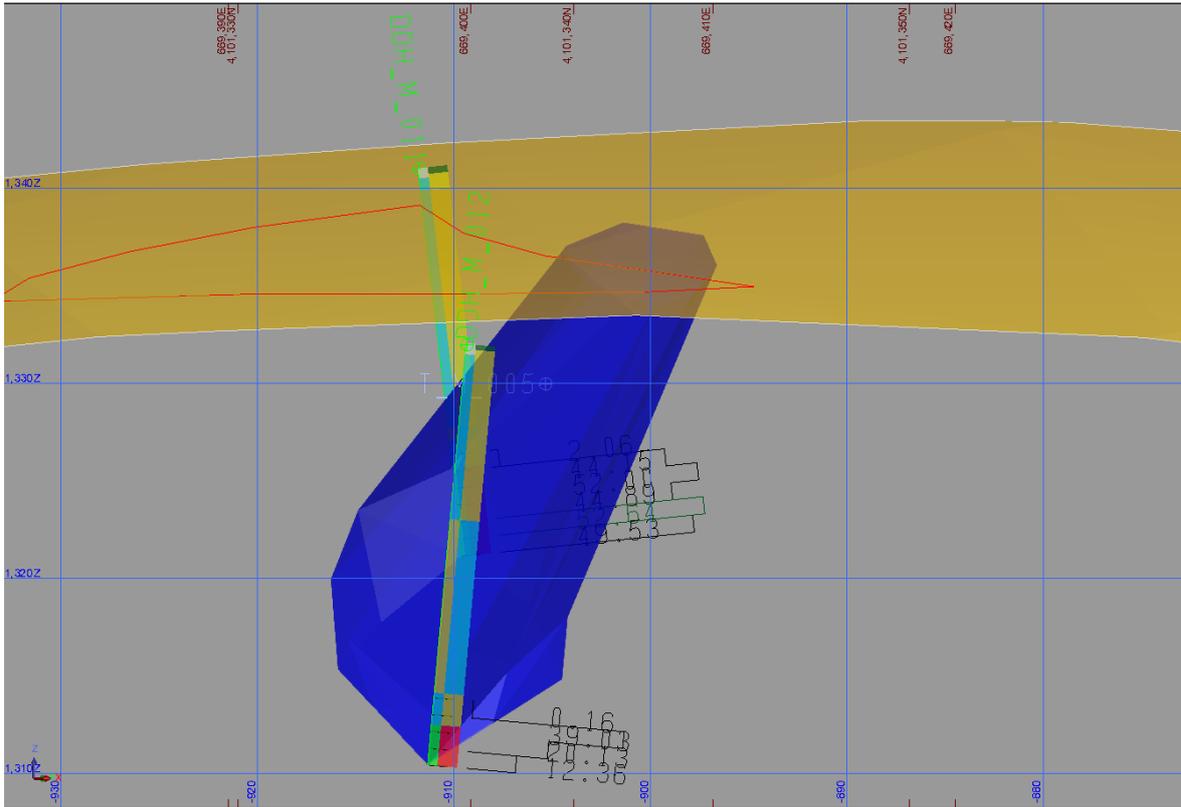

**Figure 31. Wireframe D in section (location of section line is given in Figure 30).**



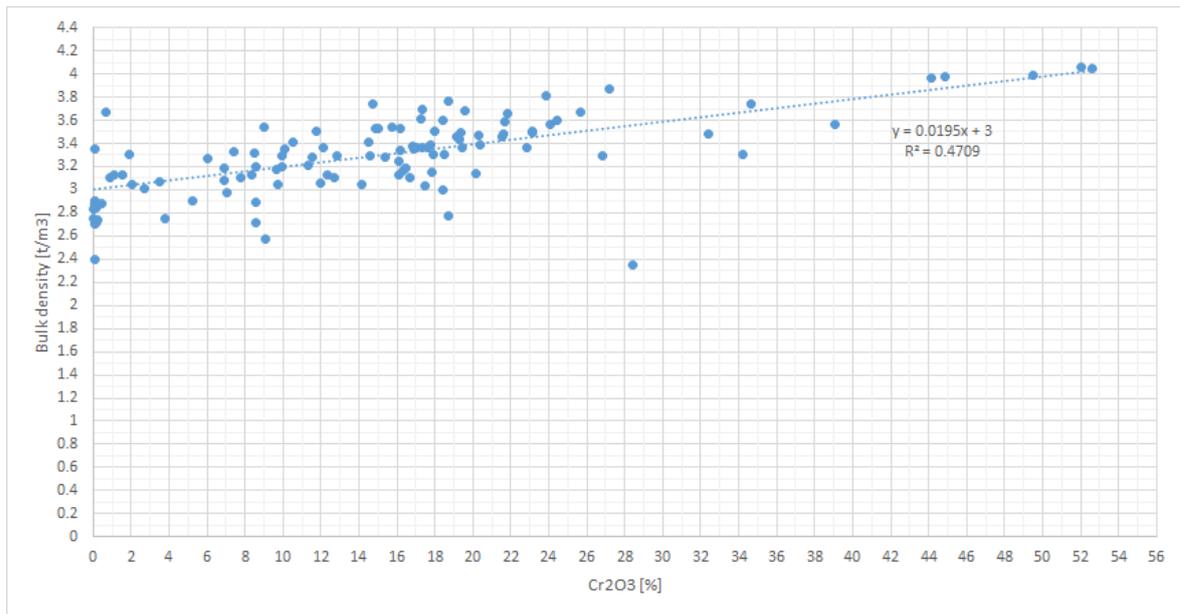

**Figure 33. Cross plot bulk density [t/m<sup>3</sup>] vs. Cr<sub>2</sub>O<sub>3</sub> [%] showing scatter.**

## 14.7 GEOSTATISTICS / INTERPOLATION METHOD

Geostatistics and data interpolation have not been done to date due the early stage of this project.

## 14.8 RESOURCE CLASSIFICATION

Resource classification is based on the confidence in the estimate regarding mainly geometry of the orebody and grade continuity.

The interpreted wireframes are based on geological logging, density data and chemical data. Even if the the geological structure of the chromite mineralization needs to be investigated in more detail, a rough estimate on geological and grade continuity can be made. In consequence the wireframes were classified as inferred resource.

Hasat's Mugla project is still an early stage project, however with very promising results from drilling. DMT's experience in the geological setting of podiform chromite deposits shows that these are complex and need detailed investigations on thickness, mineral composition and spatial distribution.

## 14.9 MODEL VALIDATION

Model validation is done in order to show that wireframed volumes meet basic geometric parameters based on drilling results and the interpretation methodology. These basic geometry parameters include average drilled thickness, length of outcrop, which is currently interpreted on the extension in the drill holes, and, finally, inclined length from surface to bottom of wireframe. It is also noted that, at this stage, it is not clear, how the holes are orientated with regards to the orientation of the chromite-rich bodies, which could affect thicknesses.

**Table 14. Validation of volumes of wireframes**

Mineralized Body	Volume of Wireframes [m <sup>3</sup> ]	Average drilled thickness [m]	Outcrop length along assumed strike	Length along assumed dip	Volume of control
A/B	8 970	12.0	30	30	11 000
C	10 160	7.5	30	40	9 000
D	2 960	4.0	20	30	2 400
<b>TOTAL</b>	22 090				20 400

## 14.10 ESTIMATE OF MINERAL RESOURCES

This report provides an inferred resource. This estimate is based on wireframes modelled based on results of geological logging, assays and densities of 11 drill holes, which intersected chromite mineralization. These wireframes are envelopes of chromite mineralization.

No block model has been done due to early stage of the project.

Several Cr<sub>2</sub>O<sub>3</sub> cut-off grades were applied to the resource database and corresponding average grades and densities were calculated. The portion of the assayed intervals was set in correspondence to the volume of wireframe, which again was used to calculate a bulk tonnage. The results of the grade-tonnage relationships are given in the following tables.

Estimated tonnages range from 74 800 t with an average Cr<sub>2</sub>O<sub>3</sub> grade of 18.5 % without any application of a cut-off grade to 3 200 t with an average Cr<sub>2</sub>O<sub>3</sub> grade of 52.3 % at a 50 % Cr<sub>2</sub>O<sub>3</sub> cut-off grade (see Table 15 to Table 18).

**For this resource estimate no cut-off grade has been applied due to the early status of the project.**

In addition, some 14 % of the resource (appr. 10 000 t) might be direct shipping ore with almost 45 % Cr<sub>2</sub>O<sub>3</sub> based on a 28 % Cr<sub>2</sub>O<sub>3</sub> cut-off grade. However, a processing study must show, if any deleterious elements are acceptable.

**Table 15. Inferred resource comprising all three bodies A/B, C and D**

Cut-off Cr <sub>2</sub> O <sub>3</sub> [%]	Density [t/m <sup>3</sup> ]	Cr <sub>2</sub> O <sub>3</sub> [%]	Tonnage [t]
0	3.39	18.54	74 800
2	3.40	19.82	69 800
4	3.41	20.27	67 800
6	3.42	20.47	66 900
8	3.44	21.50	62 100
10	3.48	22.82	56 100
12	3.49	23.76	52 000
14	3.51	24.60	48 500
16	3.52	25.80	43 200
18	3.62	30.17	28 900
20	3.67	32.74	23 500
22	3.75	36.97	17 200
24	3.79	40.33	13 800
26	3.82	43.26	11 600
28	3.84	44.98	10 500
30	3.90	45.63	10 100
32	3.90	45.63	10 100
34	3.93	46.46	9 500
36	3.98	48.03	8 400
38	3.98	48.03	8 400
40	4.01	48.67	7 800
42	4.01	48.67	7 800
44	4.01	48.67	7 800
46	4.03	51.40	4 700
48	4.03	51.40	4 700
50	4.06	52.32	3 200
52	4.06	52.32	3 200

**Table 16. Inferred resource for body A/B**

Cut-off Cr <sub>2</sub> O <sub>3</sub> [%]	Drilled Interval [m]	Density [t/m <sup>3</sup> ]	Cr <sub>2</sub> O <sub>3</sub> [%]	Volume [m <sup>3</sup> ]	Tonnage [t]
0	57.1	3.37	16.56	8 970	30 300
2	55.1	3.37	17.14	8 656	29 200
4	53.6	3.38	17.48	8 420	28 500
6	53.6	3.38	17.48	8 420	28 500
8	51.6	3.38	17.89	8 106	27 400
10	43.4	3.42	19.45	6 818	23 300
12	39.4	3.43	20.24	6 189	21 200
14	38.4	3.43	20.42	6 032	20 700
16	32.7	3.43	21.38	5 137	17 600
18	23	3.45	23.17	3 613	12 500
20	13	3.48	26.35	2 042	7 100
22	10	3.47	27.82	1 571	5 400
24	8	3.46	29.02	1 257	4 300
26	6	3.41	30.72	943	3 200
28	4	3.31	32.78	628	2 100
30	3	3.52	33.76	471	1 700
32	3	3.52	33.76	471	1 700
34	2	3.54	34.44	314	1 100

**Table 17. Inferred resource for body C**

Cut-off Cr <sub>2</sub> O <sub>3</sub> [%]	Drilled Interval [m]	Density [t/m <sup>3</sup> ]	Cr <sub>2</sub> O <sub>3</sub> [%]	Volume [m <sup>3</sup> ]	Tonnage [t]
0	32.6	3.28	13.13	10 160	33300
2	28.6	3.30	14.79	8 913	29400
4	27.6	3.30	15.17	8 602	28400
6	26.6	3.32	15.50	8 290	27500
8	22.8	3.35	16.80	7 106	23800
10	20.8	3.38	17.44	6 482	21900
12	18.8	3.39	18.14	5 859	19900
14	17	3.41	18.72	5 298	18100
16	15	3.41	19.29	4 675	15900
18	6	3.57	22.53	1 870	6700
20	6	3.57	22.53	1 870	6700
22	3	3.63	24.15	935	3400
24	1	3.67	25.67	312	1100

**Table 18. Inferred resource for body D**

Cut-off Cr <sub>2</sub> O <sub>3</sub> [%]	Drilled Interval [m]	Density [t/m <sup>3</sup> ]	Cr <sub>2</sub> O <sub>3</sub> [%]	Volume [m <sup>3</sup> ]	Tonnage [t]
0	7.6	3.77	40.01	2 960	11200
2	7.6	3.77	40.01	2 960	11200
4	7.4	3.79	40.85	2 882	10900
6	7.4	3.79	40.85	2 882	10900
8	7.4	3.79	40.85	2 882	10900
10	7.4	3.79	40.85	2 882	10900
12	7.4	3.79	40.85	2 882	10900
14	6.4	3.87	44.47	2 493	9700
16	6.4	3.87	44.47	2 493	9700
18	6.4	3.87	44.47	2 493	9700
20	6.4	3.87	44.47	2 493	9700
22	5.4	3.98	48.03	2 103	8400
24	5.4	3.98	48.03	2 103	8400
26	5.4	3.98	48.03	2 103	8400
28	5.4	3.98	48.03	2 103	8400
30	5.4	3.98	48.03	2 103	8400
32	5.4	3.98	48.03	2 103	8400
34	5.4	3.98	48.03	2 103	8400
36	5.4	3.98	48.03	2 103	8400
38	5.4	3.98	48.03	2 103	8400
40	5	4.01	48.67	1 947	7800
42	5	4.01	48.67	1 947	7800
44	5	4.01	48.67	1 947	7800
46	3	4.03	51.40	1 168	4700
48	3	4.03	51.40	1 168	4700
50	2	4.06	52.32	779	3200
52	2	4.06	52.32	779	3200

## 15 MINERAL RESERVE ESTIMATES

This is an early stage project and no mineral reserve estimate has been done.

## 16 MINING METHODS

This is an early stage project and no study on mining methods has been done.

## **17 RECOVERY METHODS**

This is an early stage project and no study on recovery methods has been done.

## **18 PROJECT INFRASTRUCTURE**

This is an early stage project and no study on the project infrastructure has been done.

## **19 MARKET STUDIES**

This is an early stage project and no market study has been done.

## **20 ENVIRONMENTAL STUDIES, PERMITTING AND SOCIAL OR COMMUNITY IMPACT**

This is an early stage project and no environmental studies have been done.

## **21 CAPITAL AND OPERATING COSTS**

This is an early stage project and no studies on capital and operating costs have been done.

## **22 ECONOMIC ANALYSIS**

This is an early stage project and no economic studies have been done.

## **23 ADJACENT PROPERTIES**

Exploration activities of adjacent properties have not been considered.

## **24 OTHER RELEVANT DATA AND INFORMATION**

No other relevant data and information is available.

## 25 INTERPRETATION AND CONCLUSIONS

The results of geological logging confirms the continuity of chromite mineralization at depth for 4 sites, two site were combined. In consequence, three wireframes were modelled.

Several Cr<sub>2</sub>O<sub>3</sub> cut-off grades were applied to the resource database and corresponding average grades and densities were calculated. The portion of the assayed intervals was set in correspondence to the volume of wireframe, which again was used to calculate a bulk tonnage.

Estimated tonnages range from 74 800 t with an average Cr<sub>2</sub>O<sub>3</sub> grade of 18.5 % without any application of a cut-off to 3 200 t with an average Cr<sub>2</sub>O<sub>3</sub> grade of 52.3 % at a 50 % Cr<sub>2</sub>O<sub>3</sub> cut-off grade.

**For this resource estimate no cut-off grade has been applied due to the early status of the project.**

In addition, some 14 % of the resource (appr. 10 000 t) might be direct shipping ore with almost 45 % Cr<sub>2</sub>O<sub>3</sub> based on a 28 % Cr<sub>2</sub>O<sub>3</sub> cut-off grade. However, a processing study must show, if any deleterious elements are acceptable.

## 26 RECOMMENDATIONS

From the above it is obvious that the interpretation methodology has to be confirmed and possibly amended, after further drilling and trenching has clarified the geological structure of the chromite mineralization. Therefore, DMT recommends to do the following work in order to clarify the geological structure of the chromite mineralization.

- Trenches will be logged geologically and sampled according to SOPs
- Detailed mapping of side walls of the trenches in order to investigate the geological structure and continuity.
- Re-survey of trenches and topographical survey around trenches.
- Electron microprobe analysis on chromite samples from weak, moderate and massive chromite mineralization should be done in order to test the chromite composition and possible variations thereof.
- Additional drilling (1000 m) based on the results of the trenching program in order to confirm understanding of the orientation and structure of the chromite minerali-

sation as well as fill-in gaps in the assay data base, produce a block model, increase the resource and probably transform some of the resource into a higher category in preparation of an economic assessment.

## 27 REFERENCES

Ozcan Yigit (2009) Mineral Deposits of Turkey in Relation to Tethyan Metallogeny: Implications for Future Mineral Exploration. *Economic Geology* (2009) 104 (1): 19-51.

I. Uysal, M. B. Sadiklar, M. Tarkian, O. Karsli, and F. Aydin (2005) Mineralogy and composition of the chromitites and their platinum-group minerals from Ortaca (Mugla-SW Turkey): evidence for ophiolitic chromitite genesis. *Mineralogy and Petrology* (2005) 83: 219–242

## Preliminary Cost and Production Schedule for Mugla Chromite License 200712070



For: Hasat BNO Grup Gıd. Yem. Hayv. Teks. İnş. San. Tic.  
A.Ş.

Date: 26.2.2018

Prepared by: Dipl.-Ing. Dirk H. Wagner



Table of Contents

1 Introduction ..... 4

2 Waste Volume ..... 4

3 Production Plan ..... 4

4 Production Approach ..... 5

5 Operating Cost ..... 5

    5.1 Mining ..... 5

    5.2 Owner’s Team ..... 5

    5.3 General & Administration ..... 5

    5.4 Licence Fee ..... 5

    5.5 Royalties ..... 6

    5.6 Transport to port ..... 6

    5.7 Contingency ..... 6

6 Capital Expenditure ..... 6

7 Cash Flow ..... 6



---

List of Tables

Table 1 – Production Plan ..... 4  
Table 2 – Cash Flow Calculation ..... 7

List of Annexes

Annex 1 – CV of Dirk H. Wagner



## 1 Introduction

Hasat BNO Grup Gıd. Yem. Hayv. Teks. İnş. San. Tic. A.Ş. (HASAT BNO) is exploring a chromite deposit in the Mugla province of Turkey.

An initial drilling program has been finalized and HASAT BNO needs to provide a status report to the government. According to local experts a volume of 74.800 t of chromite ore with 30% Cr<sub>2</sub>O<sub>3</sub> has to be expected from the deposit.

The status report should include a preliminary production and cost schedule. HASAT BNO contracted Dirk H. Wagner Mining Consulting (DHWMC) for preparing the preliminary cost and production schedule.

## 2 Waste Volume

According to local experts the deposit consists of 3 orebodies. All the ore bodies are close to surface and therefore open pit method has been selected as mining method.

Based on the assumed orebody geometry the volume of simplified open pits has been generated with a general slope angle of 60° from which the ore volume (based on an average ore density of 3.4 t/m<sup>3</sup>) was deducted. Total waste volume was calculated as 247,000 m<sup>3</sup>. Assuming a waste density of 2.5 t/m<sup>3</sup> the total waste tonnage would amount to

**618,000 t waste,**

giving a stripping ratio of

**8.3 t:t.**

## 3 Production Plan

HASAT BNO intends to produce a maximum amount of 20,000 t per year. Accordingly, the mine life would be almost 4 years (assuming high selectivity and almost zero losses and dilution).

Usually such operations require some pre-stripping to get to the ore. Therefore, the production plan as shown in Table 1 was assumed.

*Table 1 – Production Plan*

Years	1	2	3	4	Total
Ore [t]	14,800	20,000	20,000	20,000	74,800
Waste [t]	154,500	154,500	154,500	154,500	618,000
Stripping Ratio [t:t]	10.4	7.7	7.7	7.7	8.3

Pre-Stripping has been considered by reducing ore production in the first year to ¼ of the requested production rate pushing the stripping ratio in year 1 to 10.4 (t:t). In the following years the stripping ratio is going down to 7.7 (t:t).



## 4 Production Approach

The current mine life is 4 years. Such a short period requires a contractor mining approach since capital expenditures for production equipment would not be amortized over the short mine life. All works will be sub-contracted to a contractor including:

- Waste drilling and blasting
- Waste loading
- Waste haulage
- Ore drilling and blasting
- Ore crushing and screening
- Ore loading
- Ore haulage

Due to the low production of maximum 580 t per day material (waste and ore) normal sized equipment available from civil construction contractors will be sufficient for the operation.

HASAT BNO will engage a minimum team of engineers and technicians to monitor the contractor work.

## 5 Operating Cost

Cost estimate is based on experience from other similar projects, information received from HASAT BNO and estimates of DHWMC.

### 5.1 Mining

Mining cost is based on DHWMC experience from other hard rock projects in Turkey. It is assumed that mining will cost 6.1 TRY per m<sup>3</sup> of rock. This translates into 2.5 TRY/t cost for waste mining (2.5 t/m<sup>3</sup> density) and 1.8 TRY/t for ore mining (3.3 t/m<sup>3</sup> density). The ore has to be crushed and screened. For this operation a specific cost of 3 TRY/t has been assumed.

### 5.2 Owner's Team

The owner's team consists of:

- 1 Manager @ 90,000 TRY/a
- 1 Assistant @ 50,000 TRY/a
- 1 Clerk @ 50,000 TRY/a
- 2 Helpers/Workers @ 80,000 TRY/a

Total cost amounts to 270,000 TRY per year.

### 5.3 General & Administration

An amount of 75,000 TRY per year has been considered for all other general and administration cost of the operation.

### 5.4 Licence Fee

For retaining the licence, a fee of 30,694 TRY has to be paid per year. The number has been provided by HASAT BNO. In the calculations 31,000 TRY was used.



### 5.5 Royalties

According to HASAT BNO the royalty payment to governmental organisations amounts to 24.83 TRY/t per year. In the calculations 25 TRY/t was used.

### 5.6 Transport to port

The concentrate has to be trucked to the port of Iskenderun. The distance to the port is more than 900 km. The Transport cost has been estimated to 182 TRY/t by HASAT BNO.

### 5.7 Contingency

The project is still in an early stage and therefore a contingency of 15% has been applied to the operating cost excluding transport cost. Transport cost has been excluded since this cost estimate has a high accuracy.

## 6 Capital Expenditure

Due to the contractor mining concept the capital expenditures are limited. Following items have been considered:

- 500,000 TRY for road preparation
- 200,000 TRY for other infrastructure like fences, lighting, paving of a site for office containers, etc.
- 100,000 TRY per year for small items and unexpected expenditures.

## 7 Cash Flow

All above estimates have been summarized in a Cash-Flow Calculation (see Table 2).

The total revenue received from the concentrate sales is 68.5 million TRY based on a concentrate price of 916 TRY/t.

The average operating cost of the operation amounts to 70 USD/t. Including the capital expenditures a total expenditure of 74 USD/t is required for the production of the concentrate.

The project shows right from the beginning a positive Cash Flow. The total Cash Flow amounts to 47.7 million TRY.



Table 2 – Cash Flow Calculation

Exchange Rate	3.75 TRY/USD						
	Year	1	2	3	4	Total	
<b>Mine Production</b>							
Chromite	kt	14,800	20,000	20,000	20,000	74,800	
Waste	000 t	154,500	154,500	154,500	154,500	618,000	
Stripping Ratio	t:t	10.4	7.7	7.7	7.7	8.3	
<b>Revenue</b>							
Concentrate	916 TRY/t 244 USD/t	000 TRY 000 USD	13,557 3,615	18,320 4,885	18,320 4,885	18,320 4,885	68,517 18,271
<b>Operating Cost</b>							
Waste Mining (Contr.)	2.50 TRY/t	000 TRY	386	386	386	386	1,545
Chromite Mining (Contr.)	1.80 TRY/t	000 TRY	27	36	36	36	135
Concentrate Preparation	3.00 TRY/t	000 TRY	44	60	60	60	224
Owner's Team	270 000 TRY/a	000 TRY	270	270	270	270	1,080
G&A	75 000 TRY/a	000 TRY	75	75	75	75	300
License Fee		000 TRY	31	31	31	31	124
Transport to port	182.00 TRY/t	000 TRY	2,694	3,640	3,640	3,640	13,614
Royalties	25.00 TRY/t	000 TRY	370	500	500	500	1,870
Contingency	15 % of Total*	000 TRY	180	204	204	204	792
<b>Total</b>		<b>000 TRY</b>	<b>4,077</b>	<b>5,202</b>	<b>5,202</b>	<b>5,202</b>	<b>19,683</b>
		000 USD	1,087	1,387	1,387	1,387	5,249
		USD/t	73	69	69	69	70
<b>Capital Expenditures</b>							
Road Preparation		000 TRY	500				500
Other Infrastructure		000 TRY	200				200
Others		000 TRY	100	100	100	100	400
<b>Total</b>		<b>000 TRY</b>	<b>800</b>	<b>100</b>	<b>100</b>	<b>100</b>	<b>1,100</b>
		000 USD	213	27	27	27	293
<b>Cash Flow</b>							
<b>Annual</b>		<b>000 TRY</b>	<b>8,679</b>	<b>13,018</b>	<b>13,018</b>	<b>13,018</b>	<b>47,733</b>
		000 USD	2,315	3,471	3,471	3,471	12,729
Acc.		000 TRY	8,679	21,697	34,715	47,733	
		000 USD	2,315	5,786	9,257	12,729	

\*Total excluding transport to port

Brilon, 26.2.2018,



**ANNEX 1**  
**CV Dirk H. Wagner**



Dirk H. Wagner  
Mining Consulting

## **CV Dirk Wagner**

as of 01.011.2017

Briloner Tor 29  
59929 Brilon, Germany

E-Mail: [dirk@dhwmc.com](mailto:dirk@dhwmc.com)

Mobile: +49 175 357 4442  
Phone: +49 2961 744424  
Fax: +49 2961 744412



**Curriculum Vitae**

---

<b>Name of Firm</b>	Dirk H. Wagner Mining Consulting
<b>Name of Expert</b>	<b>Dirk Wagner</b>

<b>Date of Birth</b>	1965
<b>Country of Citizenship / Residence</b>	Germany

---

**Professional Education:**

<b>Institution</b>	<b>Technical University Berlin /Germany</b>
<b>Date</b>	1986 – 1992
<b>Degree / Diploma</b>	Diploma in Mining Engineering

---

### Employment Record:

Period	Employing Organisation, title/position, Contact Info
From 2016 to present	<b>self employed/Associate to DMT</b>
From 2011 to 2015	<b>DMT Consulting GmbH Essen / Germany Senior Project Manager</b>
From 2008 to 2011	<b>Bucyrus Europe GmbH Saarbrücken / Germany Senior Project Manager</b>
From 2000 to 2008	<b>IMC Montan Consulting Essen/ Germany Senior Project Manager</b>
From 1992 to 2000	<b>Sachtleben Bergbau Services GmbH Lennestadt / Germany Project Engineer, Mine Planning Department</b>

### Membership in Professional Societies:

Ring Deutscher Bergingenieure e.V. (Society of German Mining Engineers), GDMB, SME

### Language Skills:

	speaking	reading	writing
<b>German</b>		Mother Tongue	
<b>English</b>	Excellent	Excellent	Excellent
<b>Russian</b>	Good	Very Good	Average

### Other Skills / Training / Specialised Education:

Data Processing: MS Office, MS Project, MS Access, Basic Datamine Knowledge

### Key Qualifications:

- Technical and economic evaluation of underground mining projects and open-pit mining projects
- Project management
- Evaluation of tender documents
- Supervision of underground mines
- Implementing of Quality Management Systems acc. to ISO 9000 Standard

### Countries of Work Experience:

Argentina, Australia, Brazil, China, Colombia, Czech Republic, Estonia, Ethiopia, Finland, India, Ireland, Kazakhstan, Mongolia, Poland, Russia, Spain, Turkey, Ukraine, USA, Venezuela, Vietnam, Zimbabwe

### Professional Experience Record:

#### Wassoul'Or, Mali

**Year, Country** September/October 2017, Mali  
**Client** Pearl Gold AG  
**Services** Review and evaluation of open pit gold operations  
**Position in Project** Financial Expert & Mining Engineer

#### Rich Metals Group, Georgia

**Year, Country** August/September 2017, Georgia  
**Client** Bank of Georgia  
**Services** Lenders Engineer Due Diligence, review of copper and gold mines open pit and underground, long term mine plans, gold processing facilities  
**Position in Project** Cost Engineer & Mining Engineer

**Professional Experience Record:**
**Coal Mining Company, Eastern Europe**

<b>Year, Country</b>	January/February 2017, Eastern Europe
<b>Client</b>	Undisclosed
<b>Services</b>	Technical Due Diligence incl. operating cost assessment as preparation for a bid
<b>Position in Project</b>	Project Manager, Cost Engineer

**Clara Mine, Wolfach, Germany**

<b>Year, Country</b>	Since 2016, Germany
<b>Client</b>	Sachtleben Minerals
<b>Services</b>	Advisor of the Management Board, Support in: <ul style="list-style-type: none"> <li>- updating of reporting system</li> <li>- preparation of life of mine plan (LOMP)</li> <li>- preparation of economic studies</li> <li>- monitoring of strategy process</li> </ul>
<b>Position in Project</b>	Senior Advisor

**Aguas Tenidas Mine**

<b>Year, Country</b>	2016, Spain
<b>Client</b>	DMT
<b>Services</b>	Fatal Flaw Analysis
<b>Position in Project</b>	Mining Expert
<b>Input</b>	Review of mine plans and operations of 3 underground ore mines

**Vozkhod Oriel Chromite Mine**

<b>Year, Country</b>	2014 - 2015, Kazakhstan
<b>Client</b>	Yilmaden
<b>Services</b>	JORC Reserve review, Geotechnical Investigations, Health and Safety Audit preparation to support financing process. Owner's engineer
<b>Position in Project</b>	Project Manager
<b>Input</b>	Project Management, Peer Review

**Professional Experience Record:**
**Kalkim Lead-Zinc Mine**

<b>Year, Country</b>	2014 - 2015, Turkey
<b>Client</b>	CVK Maden
<b>Services</b>	Resource Estimate for a Lead Zinc Mine
<b>Position in Project</b>	Project Manager
<b>Input</b>	Project Coordination, Peer Review

**Merzifon Underground Lignite Deposit**

<b>Year, Country</b>	2013 – 2015, Turkey
<b>Client</b>	Gürmin Enerji
<b>Services</b>	Resource Estimate, Preliminary Economic Assessment and Gas Drainage concept for the Amasya / Merzifon Project of Gürmin Enerji
<b>Position in Project</b>	Project Manager
<b>Input</b>	Project management, Preliminary Mine planning, Economic Assessment

**Zonguldak Baglik-Inagzi Underground Coking Coal Project**

<b>Year, Country</b>	2013 – 2015
<b>Client</b>	Soma Holding
<b>Services</b>	Resource Estimate, Preliminary Economic Assessment and Gas Drainage Concept for the Zonguldak Project of Soma Kömür
<b>Position in Project</b>	Project Manager
<b>Input</b>	Project Management, mine planning, economic assessment, peer review of other chapters

**Gökirmag Copper Project**

<b>Year, Country</b>	2013 – 2015
<b>Client</b>	Asya Maden
<b>Services</b>	Feasibility Study on the Gökirmak Copper Project in Northern Turkey
<b>Position in Project</b>	Project Manager
<b>Input</b>	Project management, mine planning, cost calculation, cash flow modelling

### **Soma Eynez Lignite Deposit**

<b>Year, Country</b>	2013, Turkey
<b>Client</b>	Undisclosed
<b>Services</b>	Due Diligence on an underground coal mining project in Soma area
<b>Position in Project</b>	Project Manager
<b>Input</b>	Project coordination, review of Mine Plan, production plan and economic evaluation

### **Camlik, Goynukoren and Pulluca silver deposits**

<b>Year, Country</b>	2012- 2013, Turkey
<b>Client</b>	Yildizlar Holding
<b>Services</b>	Preparation of Technical Report according to NI43-101 for Eti Gümüş Silvermine, Pit Optimization
<b>Position in Project</b>	Project Manager
<b>Input</b>	Project management, pit optimization, mine planning, equipment selection, economic evaluation

### **Komorovskoje gold mine**

<b>Year, Country</b>	2012, Kazakhstan
<b>Client</b>	Kazzinc
<b>Services</b>	Investigation of In-Pit Crushing and continuous haulage systems for Komorovskoye open pit.
<b>Position in Project</b>	Project Manager
<b>Input</b>	Project management, cost calculation, mine planning

### **Paz del Rio Coal Mine**

<b>Year, Country</b>	2011 – 2012, Colombia
<b>Client</b>	Votorantim
<b>Services</b>	Underground Part of Prefeasibility Study for underground coal mine project
<b>Position in Project</b>	Mining Engineer
<b>Input</b>	Mine Planning, equipment selection

#### **La Mancha Resources**

<b>Year, Country</b>	2012, Australia
<b>Client</b>	Societe Generale
<b>Services</b>	Due Diligence on an underground and an open pit Gold Mine
<b>Position in Project</b>	Mining Engineer
<b>Input</b>	Review of mine plans, review of operations, review of costs

#### **Banphu Nickel mine**

<b>Year, Country</b>	2012 Vietnam
<b>Client</b>	Pala Investment
<b>Services</b>	Due Diligence on Underground Nickel Mine
<b>Position in Project</b>	Mining Engineer
<b>Input</b>	Review of operations, review of costs, review of Life of Mine Plan

#### **Dijon Mining**

<b>Year, Country</b>	2011, Tajikistan
<b>Client</b>	DION
<b>Services</b>	Assessment of a small scale underground mine
<b>Position in Project</b>	Project Manager
<b>Input</b>	Review of underground coal mining project

#### **Mibrag Lignite Open Pit**

<b>Year, Country</b>	2011, Germany
<b>Client</b>	Undisclosed
<b>Services</b>	Competent Persons Report on Coal assets of a German Company
<b>Position in Project</b>	Economic Expert
<b>Input</b>	Review of cost, review of business plans

**Tuncbilek underground lignite mine**

<b>Year, Country</b>	2010 – 2014, Turkey
<b>Client</b>	TKI
<b>Services</b>	Engineering Assistance, Review of FS on Tuncbilek deposit
<b>Position in Project</b>	Project Manager
<b>Input</b>	Supervision of Turkish Consultants, Mine Planning, Project Coordination (Serbian, Turkish and German team members)

**Soma Eynez Underground coal project**

<b>Year, Country</b>	2010, Turkey
<b>Client</b>	Demir Export
<b>Services</b>	Engineering Assistance on Tender preparation for Cayirhan Tender including mine planning.
<b>Position in Project</b>	Project Manager
<b>Input</b>	Review of mine plan, review of engineering, preparation of cost schedules

**KTK 7/8 coal mining project, SCCL**

<b>Year, Country</b>	2010, India
<b>Client</b>	Indu Projects
<b>Services</b>	Equipment Proposal Preparation, including mine planning
<b>Position in Project</b>	Project Manager
<b>Input</b>	Proposal coordination, mine planning

**Eniseyskaja Coal Mining Project**

<b>Year, Country</b>	2009, Russia
<b>Client</b>	EPK
<b>Services</b>	Pre-Feasibility Study on application of slice mining
<b>Position in Project</b>	Project manager
<b>Input</b>	Project Coordination, Mine Planning, economic evaluation

### **Komorovskoye Coal Mine**

<b>Year, Country</b>	2008, Russia
<b>Client</b>	Undisclosed
<b>Services</b>	Due Diligence Report on an underground Coal mine
<b>Position in Project</b>	Senior Mining Expert
<b>Input</b>	Review of mining plans and operations, review of mining costs

### **Sapadnij Kamys**

<b>Year, Country</b>	2008, Kazakhstan
<b>Client</b>	Undisclosed
<b>Services</b>	Reserve assessment for Manganese projects
<b>Position in Project</b>	Senior Mining Expert
<b>Input</b>	Review of Mine plan, review of mining cost, review of operations

### **Eurasia Gold**

<b>Year, Country</b>	2008, Kazakhstan
<b>Client</b>	Kazakhmys
<b>Services</b>	Reserve assessment for all operations of “Kazakhmys Gold”
<b>Position in Project</b>	Senior Mining Expert
<b>Input</b>	Review of mining operations, review of mining cost, review of life of mine plan

### **Cerattepe Copper Mine Project**

<b>Year, Country</b>	2007/8, Turkey
<b>Client</b>	CBI (Cayeli Bakir)
<b>Services</b>	EPCM Project on an underground copper mine
<b>Position in Project</b>	Project Manager
<b>Input</b>	Project coordination, supervision of surface civil construction, specification of works, tender preparation

### **MSOL Gold Mines**

<b>Year, Country</b>	2007, Brazil
<b>Client</b>	Undisclosed
<b>Services</b>	Due Diligence on several small gold mining operations in Brazil
<b>Position in Project</b>	Senior Mining Expert
<b>Input</b>	Review of Mining operations, review of life of mine plan, review of costs

### **Burnstone Gold Project**

<b>Year, Country</b>	2007, South Africa / USA (Nevada)
<b>Client</b>	Undisclosed
<b>Services</b>	Due diligence on two gold mining projects
<b>Position in Project</b>	Senior Mining Expert
<b>Input</b>	Review of Mining operations, review of life of mine plan, review of costs

### **San Jose Mine**

<b>Year, Country</b>	2006, Argentina
<b>Client</b>	Hochschild PLC
<b>Services</b>	Reserve Evaluation San Jose gold Mine
<b>Position in Project</b>	Project Manager
<b>Input</b>	Review of reserve Estimate, review of modifying factors

### **DTEK Coal Mines**

<b>Year, Country</b>	2006, Ukraine
<b>Client</b>	DTEK
<b>Services</b>	Optimisation of underground coal mines and methane utilization of 11 underground coal mines.
<b>Position in Project</b>	Dep. Project Manager
<b>Input</b>	Project Coordination

**Aguas tenidas Mine**

<b>Year, Country</b>	2005/06, Spain
<b>Client</b>	Investec Bank
<b>Services</b>	Due Dilligence for a Polymetallic Project in Spain
<b>Position in Project</b>	Senior Mining Engineer
<b>Input</b>	Review of Feasibility Study, review of economic model and mine planning

**JSW coal mines**

<b>Year, Country</b>	2005, Poland Upper Silesia
<b>Client</b>	World Bank
<b>Services</b>	Efficiency improvement of selected Polish hard coal mines
<b>Position in Project</b>	Senior Mining Engineer
<b>Input</b>	Review of Mining Operations, review of mine efficiency